

Review

<https://doi.org/10.48130/bchax-0025-0008>

Engineered biochar for simultaneous removal of heavy metals and organic pollutants from wastewater: mechanisms, efficiency, and applications

Nana Wang¹, Bing Wang^{1,2*}, Hailong Wang^{3,4}, Pan Wu^{1,2}, Masud Hassan², Shengsen Wang⁵ and Xueyang Zhang⁶

Received: 25 July 2025

Revised: 21 August 2025

Accepted: 17 September 2025

Published online: 31 October 2025

Abstract

Organic compounds and heavy metals constitute two major classes of aquatic contaminants. Their prolonged simultaneous presence facilitates complexation reactions, which can generate novel toxicants with enhanced biological hazards. Therefore, developing advanced remediation technologies for the concurrent elimination of these remains imperative. As a carbon-rich material, biochar is considered an environmentally friendly and cost-effective adsorbent. Over the past decade, modification of biochar has emerged as a hot research topic. Strategic architectural and physicochemical modifications enable tailored surface properties and enhanced adsorption mechanisms, substantially expanding potential applications across environmental remediation domains. Despite emerging literature on the simultaneous removal of heavy metals and organic pollutants through engineered biochar, most research still focuses on the removal of single pollutants. This review examines the simultaneous removal of heavy metals and organic contaminants using functionalized biochar. Firstly, remediation efficiency, mechanistic pathways, and practical applications of engineered biochar are investigated for complex pollution matrices in aqueous environments. Secondly, physicochemical processes governing simultaneous contaminant capture through surface-modified carbon architectures are elucidated. Thirdly, performance across diverse wastewater treatment scenarios are evaluated, and environmental deployment viability assessed. This comprehensive analysis not only advances scientific understanding but also facilitates technological implementation of engineered biochar for the simultaneous removal of heavy metals and organic pollutants from wastewater.

Keywords: Engineered biochar, Heavy metals, Organic pollutants, Simultaneous removal, Application potential, Wastewater pollution


Highlights

- Engineered biochars enable simultaneous removal of organic and metallic contaminants.
- Co-adsorption occurs via bridging interactions and competitive binding mechanisms.
- Tailored biochar modifications address diverse environmental pollution scenarios.
- Performance metrics establish biochar viability across varied remediation applications.
- Strategic roadmap identifies critical research priorities for biochar advancement.

* Correspondence: Bing Wang (bwang6@gzu.edu.cn)

Full list of author information is available at the end of the article.

Graphical abstract

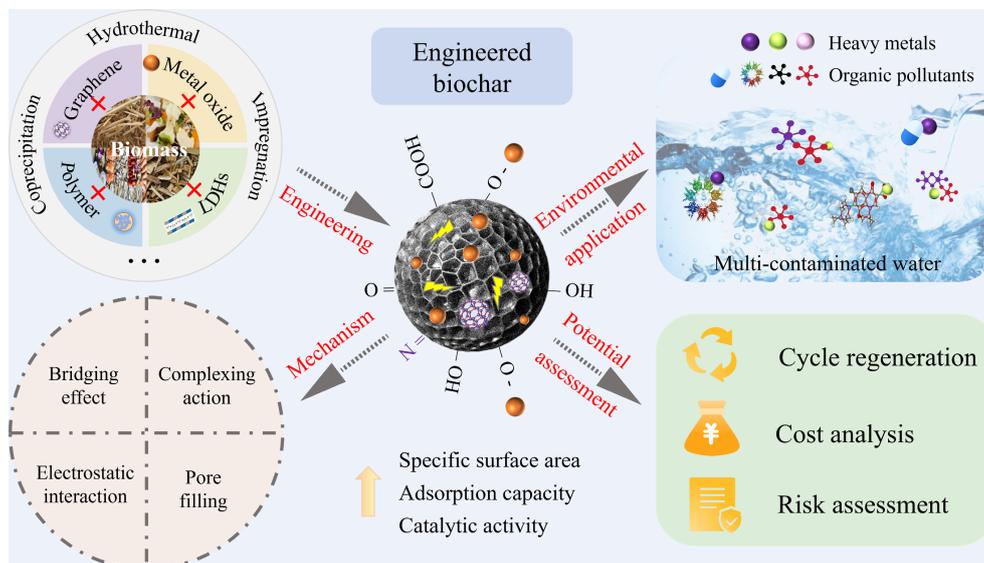

Introduction

Numerous contaminants, including heavy metals, nutrients, and emerging pollutants, are inevitably released into the aquatic environment due to the fast development of industry, agricultural production, and human activities^[1,2]. Most untreated or partially treated industrial and domestic wastewater is a major source of water pollution^[3]. Water contamination by organic pollutants and heavy metals represents a ubiquitous global challenge. Heavy metals exhibit persistent non-biodegradability, widespread distribution, and pronounced toxicity. Heavy metal discharge occurs extensively worldwide, severely compromising aquatic ecosystems and water quality^[4].

The impact of organic pollution in the aquatic environments cannot be overlooked^[5,6]. Organic pollutants include both conventional and emerging contaminants^[7]. Traditional organic compounds like dyes raise water turbidity, impede photosynthesis^[8], and may degrade into toxic or carcinogenic substances^[9]. Moreover, polycyclic aromatic hydrocarbons (PAHs) exhibit carcinogenicity toward the skin, lungs, and bladder epithelium^[10]. Emerging pollutants include pharmaceutical residues^[11], phenolic derivatives^[12], and perfluorinated compounds^[13], among others. Pharmaceuticals have the potential to promote antibiotic resistance genes, creating long-term risks to aquatic ecosystems^[14,15]. Phenolic compounds are typically utilized in the preparation of petrochemicals, synthetic rubber, and plastics. They are highly toxic to humans and can seriously affect the nervous system^[16]. Perfluorinated compounds demonstrate multiple toxicological effects, including immunosuppression, liver damage, and carcinogenic potential^[17]. While individual removal of organic pollutants or heavy metals can be achieved effectively, their simultaneous presence in aquatic systems presents substantial remediation challenges requiring integrated treatment approaches.

For simultaneous treatment of organic pollutants and heavy metals in wastewater, several techniques have been reported, such as membrane filtration^[18], ion exchange^[19], electrochemical^[20], biological^[21], and advanced oxidation methods^[22]. However, significant limitations constrain industrial implementation of these methods, including substantial operational expenses and complex integration of multiple technologies^[23]. Adsorption remains the

most promising remediation approach due to its operational simplicity, straightforward implementation, and effective regeneration potential^[24]. At present, materials frequently utilized for the adsorption of organic pollutants include montmorillonite^[25], zeolite^[26], and graphene oxide^[27]. The adsorption materials for heavy metals mainly include sepiolite^[28], chitosan^[29], biochar^[30], and carbon nanotubes^[31]. Carbonaceous materials, including carbon nanotubes, biochar, and activated carbon, facilitate the simultaneous removal of organic pollutants and heavy metals, though optimal adsorbents for these contaminant classes exhibit distinct physicochemical properties. Therefore, the development of materials with dual properties at the same time is essential for the simultaneous removal of combined pollution in wastewater.

Biochar is a stable, porous, carbon-rich material^[32,33]. As a novel kind of adsorbent, it has been extensively employed to eliminate both organic and inorganic contaminants from water^[34,35]. Typically, the physicochemical characteristics of biochar can be modified via modification^[36], giving it excellent adsorption capacity^[37,38]. For example, corn straw biochar treated with H_3PO_4 exhibited both higher pollutant adsorption capacity and higher tolerance to co-existing salts compared to untreated corn straw biochar. Bisphenol A and Cr^{6+} demonstrated maximum adsorption capabilities of 476.19 and 116.28 mg/g, respectively^[39]. The tetracycline and Pb^{2+} adsorption on manganese-enriched merchant land biochar showed superior removal efficiencies over the pristine merchant land biochar, with 279.33 and 47.51 mg/g adsorption capacity for Pb^{2+} and tetracycline, respectively. This enhancement was primarily attributed to the formation of manganese oxide and manganese minerals through pyrolysis^[40]. Therefore, an increasing number of engineered biochars are being employed for removing organic pollutants and heavy metals, such as nano-metal oxide biochar composites, magnetized biochar composites, and loaded biochar as photocatalysts, which have been developed and utilized^[41].

Although numerous biochar variants have been engineered for mixed contamination, their structural properties and remediation efficacies vary considerably. A Web of Science analysis using keywords 'biochar', 'organic pollutants', and 'heavy metals' reveals accelerating research interest in biochar-based simultaneous removal technologies (Fig. 1). Hu et al.^[42] explored the use of

biochar-based materials for removing organic and inorganic pollutants. Their work specifically examined these materials' roles in both adsorption and degradation processes. Akash et al.^[43] published a review on the application of metal-oxide nano-biochar materials for removing dyes and heavy metals. Kasera et al.^[44] discussed the adsorption mechanisms for the removal of heavy metals and organic compounds by nitrogen-doped biochar, including the mathematical analysis of adsorption. All of these studies have proved the promising advantages of biochar in certain aspects of environmental applications. Although some researchers have published reviews on the removal of organic pollutants and heavy metals, these studies mostly emphasize removal performance and mechanisms within isolated systems. Consequently, the existing research remains fragmented and insufficient to support further investigations. Therefore, a systematic summary of the simultaneous removal of organic pollutants and heavy metals by engineered biochar would help understand and grasp future research work in this field.

Based on these considerations, this review aims to: (1) examine prevalent engineered biochar for removing organic pollutants and heavy metals from wastewater; (2) elucidate simultaneous removal mechanisms for different categories of pollutants; (3) evaluate engineered biochar applications in the simultaneous removal of heavy metals and dyes, antibiotics and heavy metals, and other compounds; (4) assess practical implementation in real water systems, including regeneration techniques, economic feasibility, and environmental impacts; and (5) identify research gaps and future directions.

Engineered biochar for the simultaneous removal of heavy metals and organic pollutants from water

Transforming solid waste from agriculture, industry, and forestry into biochar to remediate polluted water is currently a practical task of turning waste into treasure. However, to achieve industrial application, functionalization of pristine biochar is required to enhance its adsorption efficiency, stability, and recyclability^[45]. Based on the literature review, engineered biochar that is utilized to remove heavy metals and organic pollutants simultaneously can be grouped into

several categories as illustrated in Fig. 2, including metal oxide-biochar composites, layered double hydroxide-biochar composites, polymer-biochar composites, and graphene-biochar composites.

Metal oxide-biochar composites

Metal oxide particles serve as the primary source of active sites that govern both adsorption capacity and catalytic turnover in biochar-based systems. Their intrinsic crystal phase, surface hydroxyl density, and redox potential ultimately determine the composite's adsorption capacity or catalytic ability toward heavy-metal ions and refractory organics^[46]. However, most metal oxides are prone to agglomeration due to their nanoscale size, and incorporating them into biochar matrices can reduce particle aggregation while improving their stability^[47]. Research reports demonstrate that functionalizing metal oxides with amino ligands enhance their functionality. Additionally, forming stable complexes with the -NH₂ and -COOH of biochar improves the hydrophilicity, dispersibility, and surface adsorption capacity of metal oxides^[48]. When selecting metal oxides for modifying pristine biochar, priority should be given to some non-toxic and environmentally friendly metal oxides, such as ZnO, Fe₃O₄, CeO₂, and ZrO₂^[49–51]. Moreover, some metal oxide particles exhibit magnetic properties and can be separated easily via a magnetic field after contaminant adsorption, enhancing their effectiveness in recovery and reuse^[52].

Common methods for preparing metal oxide-biochar composites include the sol-gel method, impregnation method, hydrothermal method, and co-precipitation method^[53]. Among these, the impregnation method is predominant due to its precise control, cost-effectiveness, and operational simplicity^[54]. This process facilitates the adsorption of metal ions onto the biochar through interaction with functional groups (e.g., -OH and -COOH) on the biochar surface. Subsequent heat treatment converts the adsorbed metal ions into metal oxides, which are then fixed onto the biochar^[55,56]. However, excessive loading of metal oxides can block the pores of the biochar, compromising its removal performance. Table 1 presents the optimal conditions for various metal oxide-biochar composites.

Compared to pristine biochar, metal oxide-biochar composites exhibit superior adsorption capabilities for both organic pollutants and heavy metals. By adjusting the types and contents of metal oxides, as well as the preparation conditions of the biochar, the adsorption performance can be adjusted to suit the removal of various water pollutants^[57]. However, the synthesis of metal oxide-biochar composites is often complex, which increases costs and limits their viability for large-scale implementation^[58]. Preparation methods for these composites require optimization to enhance their adsorption capacity and cost-effectiveness, for example, by changing carbonization conditions and improving the loading method of metal oxides. In addition, different metal oxides exhibit different affinities for particular pollutants, necessitating careful selection based on specific contamination scenarios.

Layered double hydroxide-biochar composites

Layered double hydroxides (LDHs) are a group of inorganic compounds that have a layered structure. Their chemical formula can be denoted as $[M^{2+}_{1-x}M^{3+}_x(OH)_2]^{x+}[A_{x/n}H_2O]^{n-}$, in which, M²⁺ and M³⁺ represent the divalent and trivalent metals, x denotes the ratio of M³⁺/(M³⁺ + M²⁺), and Aⁿ⁻ stands for the organic or inorganic anions^[59]. The interlayer anions in LDHs may be displaced by other heavy metal ions or other harmful ions via ion-exchange to achieve effective removal of pollutants, and thus are widely used as adsorbent materials^[60]. By preparing composites with biomass waste containing oxygen functionalized groups, the dispersion of LDHs can be

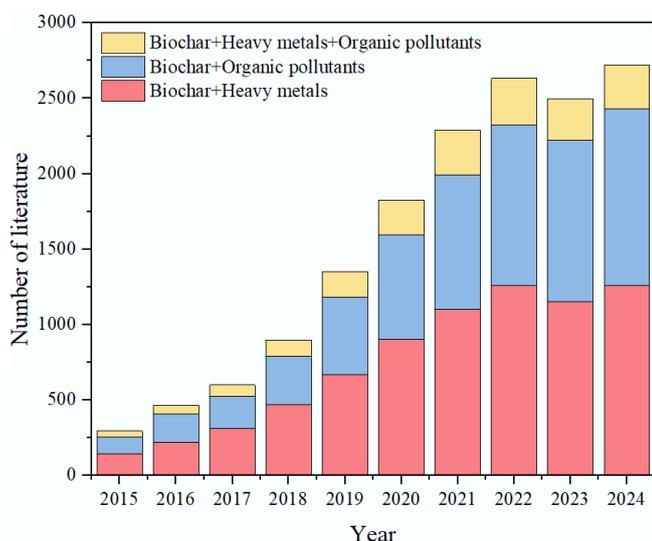


Fig. 1 The number of literature on the application of biochar in water from 2015 to 2024 (Data come from Web of Science).



Fig. 2 Different engineered biochars for the co-removal of heavy metals and organic pollutants.

Table 1 Performance and optimal conditions of engineered biochar for simultaneous removal of organic pollutants and heavy metals

Engineered biochars	Pollutants	Removal performance (mg/g)	pH	Dosage (g)	Initial concentrations (mg/L)	Reaction time (min)	Reaction temperature (°C)	Ref.
Hydroxyapatite-modified cod bone biochar	Diclofenac	43.29	8.0	0.01	100	300	-	[172]
	Fluoxetine	12.53			100			
	Pb ²⁺	714.24			2,100			
Silicon dioxide/biochar (corn cob) nanocomposite	U ⁶⁺	255.10	5.0	0.6	10–100	-	25	[173]
	Cr ⁶⁺	90.01	2.0	0.2				
	MB	1,614.04	7.0	0.4				
Potassium ferrate-activated wheat straw biochar	Cu ²⁺	48.75	-	0.2	10	720	25	[127]
	SMZ	51.72						
Magnesium oxide/rice husk biochar composite	BPA	18.10	5.0	0.1	20–160	240	25	[174]
	Cu ²⁺	64.90						
Mixed silicate/hydrocarbon (pine sawdust) composites	Cu ²⁺	214.70	-	0.5	10–300	-	-	[175]
	Zn ²⁺	227.30						
	TC	361.70						
Iron/nitrogen co-doped rapeseed straw biochar	CIP	46.45	2.0–6.0	0.2	50	-	25	[176]
	Cu ²⁺	30.77						
EDTA/chitosan bifunctionalized magnetic biochar	MO	305.4	5.0	0.5	200	-	25–45	[116]
	Cd ²⁺	63.20			100			
	Zn ²⁺	50.80			100			
Eagnetically-modified <i>Enteromorpha prolifera</i> -based biochar hydrogels	MO	47.65%	3.0	0.01	80	-	-	[177]
	Cr ⁶⁺	42.50%				80		
Polymethyl methacrylate/(rice husk ash)/polypyrrole composite film	Cr ⁶⁺	360.50	2.0	0.006	0–80	150	25	[178]
	Tartrazine (E102)	165.70				60		
Polyacrylic acid modified tobacco stem biochar	Quinclorac	80.74%	-	0.008	10	240	25	[179]
	Pb ²⁺	73.20%						
Iron/zinc activated rice straw biochar	17β-estradiol	123.00	-	0.006	6	-	25	[180]
	Cu ²⁺	76.00			140			
Nano zero valent iron loaded biochar	Cr ⁶⁺	30.87	3.0	0.3	50	2,880	25	[181]
	TCE	32.32			10			

improved, the exposure of surface active sites can be increased, and the adsorption capacity of single-LDHs can be enhanced^[61].

The preparation techniques of the hydrothermal method, the anion exchange method, the co-precipitation method, and *in-situ* synthesis are primarily applied to synthesize LDHs-biochar composites^[62]. Co-precipitation is the preferred approach for

preparing composites owing to its simplicity, economy, and high yield. The basic principle of the co-precipitation method is the reaction of divalent and trivalent metal ions with hydroxyl ions to produce LDH structures under alkaline conditions. Meanwhile, the incorporation of biochar provides a carrier that promotes the uniform deposition of LDHs on its surface^[63,64]. Nevertheless,

sometimes the inhomogeneity of the biochar surface may lead to non-uniform distribution of the LDH layer. Consequently, various LDH-biochar composites, and their optimal conditions for the elimination of organic pollutants and heavy metals, are given in Table 1.

LDHs-biochar composites exhibit selective adsorption ability due to the interlayer voids of LDHs and the porous structure of biochar, which can efficiently remove specific types of heavy metals and organic pollutants^[65]. Factors such as loading ratio, dispersion, and surface modification of layered hydroxides and biochar all affect the properties of organic pollutants and heavy metals removal^[66]. Therefore, future research should delve into these factors to optimize the composition and structure of LDH-biochar composites. Additionally, exploring regeneration and recovery methods for LDH-biochar composites is crucial for minimizing waste generation, and enhancing the sustainability of adsorption materials.

Polymer-biochar composites

Polymer-biochar composites generate synergistic effects by combining the structural integrity and chemical functionality of polymers with the porous structure and high adsorptive performance of biochar^[67]. This combination not only strengthens the stability of the composite but also effectively eliminates organic contaminants and heavy metals through chemical and physical pathways. Consequently, these composites are increasingly gaining attention in water treatment and environmental purification^[68]. Commonly used polymer materials include polyethylene, polyurethane, polyacrylamide, chitosan, and alginate^[69–71]. Among them, chitosan is particularly favored for making polymer biochar composites due to its good water solubility, biocompatibility, and ease of integration with materials like biochar^[72]. The incorporation of biochar with chitosan typically involves dispersing biochar powder in a chitosan solution, followed by solidification through freezing or heat treatment. This method embeds biochar within the chitosan polymer network, increasing the specific surface area of the composite and its adsorption sites^[73]. However, chitosan has some limitations, such as high solubility in an acidic environment, and limited mechanical strength^[74,75].

Polymer-biochar composites usually have good recyclability and can be reused multiple times through simple regeneration steps^[71]. However, some polymers may lose stability under extreme environmental conditions, affecting their adsorption performance and reusability^[76]. Therefore, appropriate modification measures can be taken, such as introducing active groups and cross-linking treatment, to increase adsorption sites and specific surface area, thereby improving adsorption performance. Alternatively, they can be incorporated with other materials, such as metal oxides and nano-materials, to enhance selectivity.

Graphene-biochar composites

In the last few years, graphene-based composites have been extensively employed in wastewater remediation owing to their outstanding chemical stability, electrical conductivity, and strong adsorption capacity^[77]. However, the high production cost of graphene and the difficulties associated with its recycling and reuse limit its sustainability. Therefore, to develop more cost-effective composites, functionalization of graphene should be considered^[78]. Studies indicate that graphene-biochar composites can reduce graphene stacking, enhancing the stability and dispersibility of the composites in water. Moreover, the incorporation of biochar can decrease the total cost of the composites and enhance their overall adsorption capacity^[79,80]. Common methods used to prepare graphene-biochar composites include physical mixing, co-precipitation, chemical cross-linking, and

solvothermal methods^[81]. The primary mechanisms for heavy metals and organic pollutants removal by graphene-biochar composites include ion exchange, π - π interactions, electrostatic effects, and pore filling^[82]. To understand the effectiveness of the composites in applications, a variety of graphene-biochar composites and polymer-biochar composites for organic pollutants and heavy metals removal are listed in Table 1.

Due to the high conductivity and excellent mass transfer properties of graphene, graphene-biochar composites exhibit a rapid adsorption rate, enabling efficient pollutant removal^[83]. Nevertheless, the preparation cost of graphene-biochar composites is relatively high, which may limit their economic feasibility in large-scale applications^[78]. In addition, the integration of graphene and biochar may pose stability challenges, especially under some extreme environmental conditions, which may lead to the detachment or aggregation of the loaded graphene and compromise adsorption performance.

Mechanisms of simultaneous removal of heavy metals and organic pollutants by engineered biochar

The main removal mechanisms of heavy metals and organic pollutants by engineered biochar are shown in Fig. 3. Electrostatic attraction is the predominant mechanism for heavy metal removal by engineered biochar. Comprehensive mechanistic analyses have additionally revealed multiple concurrent pathways contributing to adsorption phenomena, including cation- π interaction, complexation, surface precipitation, and ion exchange^[84]. π -electron donor-acceptor (EDA) interactions, electrostatic forces, hydrogen bonding, pore-filling, and hydrophobic interactions may occur in the sorption of organic pollutants^[85,86]. The adsorption mechanisms of diverse types of organic pollutants and heavy metals in the environment are very different. These variations depend on factors such as the preparation conditions of engineered biochar, environmental pH, temperature, and pollutant concentration^[87]. The impact weights are shown in Fig. 4. Complex interactions, such as enhancement, inhibition, and neutral effects, occur between organic pollutants and heavy metals^[88]. Their combined removal mechanisms include bridging effect, competitive adsorption, electrostatic interaction, and pore filling.

Bridging effect

The bridging effect is the primary mechanism facilitating the simultaneous adsorption of heavy metals and organic pollutants^[89]. Metal ions or organic ligands that are adsorbed on the engineered biochar surface act as bridges to form ternary complexes with heavy metals and organic pollutants. The formation of these complexes enhances the affinity of organic pollutants and heavy metals for the engineered biochar^[40,90]. Additionally, other organic pollutants can also directly bind with heavy metals to form complexes. In this scenario, both organic pollutants and heavy metals can act as bridges for each other, improving adsorption capacity^[91]. Through the bridging effect, more effective adsorption sites are created on the engineered biochar surface, aiding in the simultaneous removal of more heavy metals and organic pollutants.

It is worth mentioning that the bridging effect involves two distinct modes of complexation: inner-bound complexation, and outer-bound complexation^[92]. Inner-bound complexation mainly combines the central ion with the ligand through coordination bonds^[93], while outer-bound complexation connects metal acid ions to the carbon-based substrate surface via electrostatic

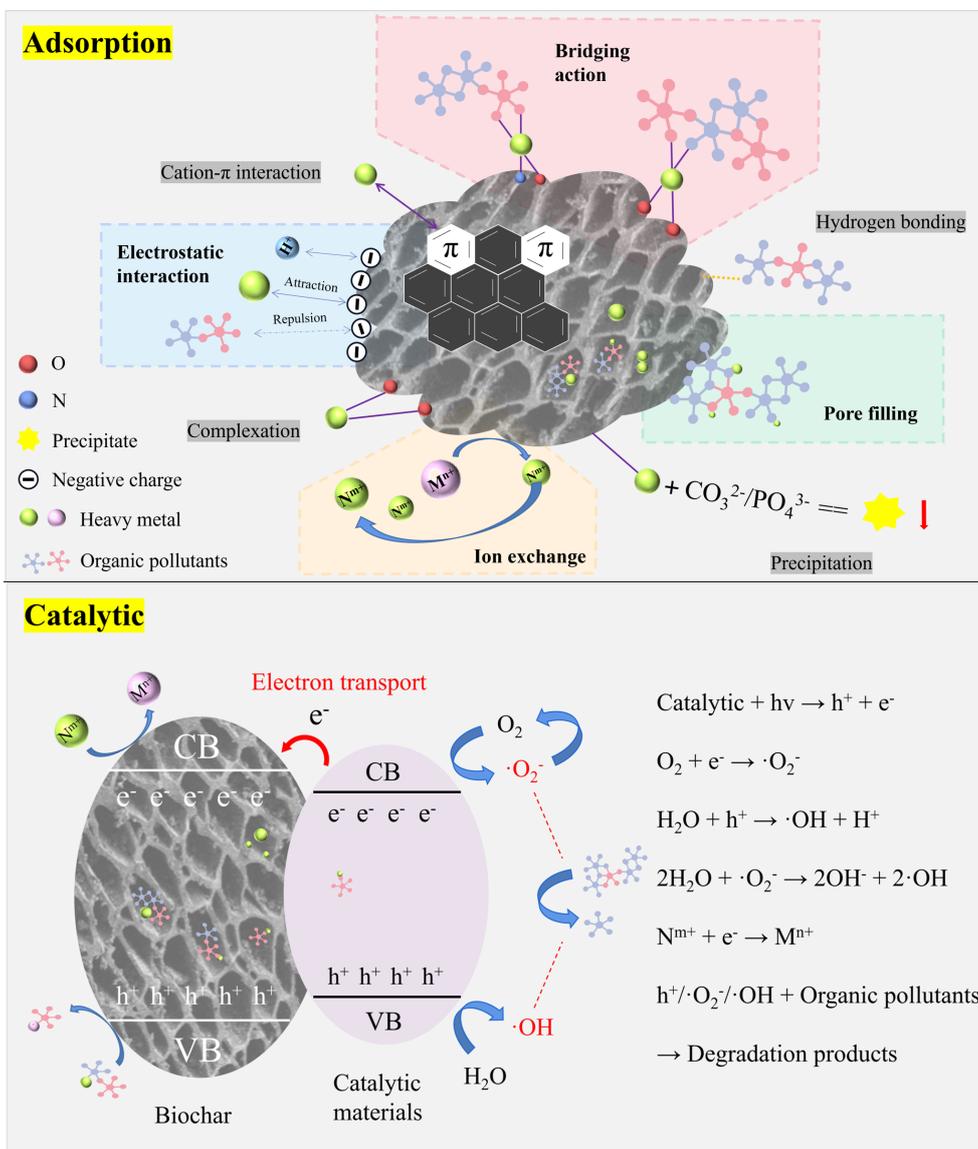


Fig. 3 Multiple mechanisms of engineered biochar for co-removing heavy metals and organic pollutants.

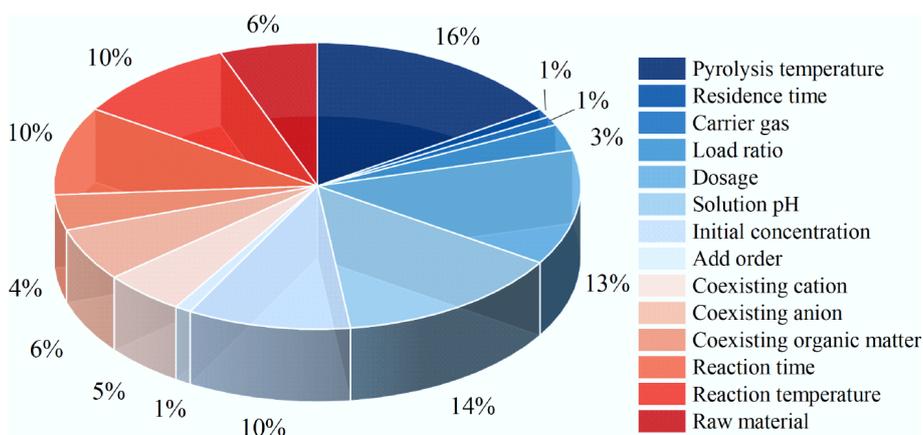


Fig. 4 The proportion of influencing factors on the removal performance of engineered biochar in co-removing heavy metals and organic pollutants.

interaction^[94]. For instance, Yea et al.^[95] investigated the impact of heavy metals on the removal of perfluorinated compounds by polyaniline-activated biochar. The results showed that heavy metals

can act as bridging ions to form inner adsorbent-heavy metal surface complexes, which improved the removal performance of perfluorinated compounds.

Competitive adsorption

Competitive adsorption of organic pollutants and heavy metals primarily involves competition for the limited active sites on engineered biochar^[96]. On the one hand, heavy metals and organic pollutants can attach to engineered biochar surfaces through different mechanisms, such as interactions with amino or carboxyl groups^[97]. For example, tetracycline adsorbs to hydroxyl groups of the charcoal via hydrogen bonding, while Cu^{2+} also adsorbs to the same groups through complexation, resulting in lower adsorption capacity in a binary system, in contrast to a single system^[98]. On the other hand, different organic pollutants and heavy metals possess distinct chemical properties, such as charge and polarity. These characteristics affect their affinity for specific functional groups on biochar^[99]. For instance, positively charged heavy metals (such as Pb^{2+} and Cu^{2+}) may be attracted to negatively charged groups like carboxyl or phenolic hydroxyl, while nonpolar organic pollutants (such as benzene) might interact with the carbon-based groups of biochar through hydrophobic interactions^[100–102].

Furthermore, when active sites on the engineered biochar are filled with either organic pollutants or heavy metals, the adsorption of other contaminants is limited. For instance, if the heavy metal ions are in high concentration, they may adsorb preferentially by ion exchange, thus suppressing the adsorption of organic pollutants^[84,103].

Electrostatic interaction

Electrostatic interaction is also an underlying mechanism. The surface charge of engineered biochar is determined by the ionization state of the functional groups on its surface, which is governed by pH^[104]. The charge properties of the biochar surface change under varying pH conditions. For instance, $-\text{COOH}$ may become protonated to $-\text{COOH}_2^+$, causing the surface of the biochar to be positively charged at low pH^[86]. Conversely, $-\text{COOH}$ may lose protons to become $-\text{COO}^-$, making the surface charge negative at high pH^[105]. These variations directly influence the engineered biochar adsorption of charged heavy metals and organic pollutants. Studies have shown that when engineered biochar surfaces and metal ions carry opposite charges, electrostatic attraction could improve the adsorption of metal ions. Meanwhile, if negatively charged organic pollutants are present in the solution, the appropriate electrostatic repulsion might reduce the adsorptive properties of the engineered biochar towards these organic pollutants. The presence of metal ions can facilitate organic pollutants removal by decreasing electrostatic repulsion between engineered biochar and organic pollutants^[106]. Additionally, the ionic strength of the solution affects electrostatic interactions. High ionic strength generally compresses the bilayer, reducing the effective charge density on the surface of engineered biochar, thereby diminishing electrostatic attraction^[107]. This means that in high-salt environments, even though metal ions or organic pollutants are electrostatically attracted to the engineered biochar surface, the adsorption efficiency may still be reduced.

Pore filling

Besides the above-mentioned mechanisms, pore filling in engineered biochar is also a significant mechanism for controlling organic pollutants and heavy metals migration^[108]. Choudhary et al.^[109] utilized NaOH-modified cactus biochar for removing malachite green, Cu^{2+} , and Ni^{2+} , with adsorption amounts of 1,341, 49, and 44 mg/g. Adsorption kinetics analyses revealed dual interaction mechanisms between NaOH-modified cactus biochar and multiple contaminants (malachite green, Cu^{2+} , Ni^{2+}): robust chemisorption processes coupled

with predominant intraparticle diffusion into microporous networks. In complementary research, Zhao et al.^[39] demonstrated phosphoric acid-modified corn stover biochar exhibiting exceptional removal efficiency toward both endocrine-disrupting bisphenol A and Cr^{6+} . The study found that phosphoric acid-modified corn stover biochar had extremely high porosity, and micropore filling was the fundamental mechanism. Cr^{6+} and bisphenol A were removed by up to 70% and 90%. Zhou et al.^[98] reported that the highest adsorption capacities of Cu^{2+} and tetracycline on iron/zinc-modified sawdust biochar were 108 and 95 mg/g at a pH of 6.0, and suggested that the pore structure of iron/zinc-modified sawdust biochar was one of the primary mechanisms influencing the high tetracycline and Cu^{2+} adsorption.

Overall, the mechanisms for the simultaneous removal of organic pollutants and heavy metals mainly include the bridging effect, competitive adsorption, electrostatic interaction, and pore filling. However, in practical applications, environmental factors are complex and varied. To better explain the adsorption mechanism of heavy metals and organic pollutants in coexistence systems, the following methods can be further explored in the future: (1) optimize experimental design, such as setting up preloaded pollutants to observe the effect; (2) establish a model and quantify the contribution ratios of internal and external bond complexation in bridging effect using *in-situ* characterization techniques; and (3) use molecular dynamics simulation combined with *in-situ* characterization techniques to map the spatial distribution and affinity of functional groups on the surface of engineered biochar, and reveal the competitive priority. In addition, future research should break through the perspective of a single mechanism, focus on the analysis of multi-mechanism coupling effects, and promote the transformation of engineered biochar from laboratory mechanism research to large-scale applications in actual wastewater treatment.

Applications of engineered biochar for the simultaneous removal of organic pollutants and heavy metals

The interactions between organic pollutants and heavy metals tend to alter their physicochemical properties, migration and transformation pathways, as well as biotoxicity^[70]. This makes the treatment of combined pollution more difficult and poses a greater threat to the environment than mono-contamination^[110]. Compared with other adsorption materials, high adsorption performance and environmental friendliness are two benefits of engineered biochar. Applications of engineered biochar have been made to remove many contaminants, including heavy metals, nutrients, emerging pollutants, and organic dyes. Therefore, the use of engineered biochar in environmental remediation is covered in depth in this section (as shown in Fig. 5).

Organic dyes and heavy metals

The printing and dyeing industries have grown rapidly in the past few years, leading to an increasingly complicated problem of water contamination from heavy metals and organic dyes^[111]. Heavy metals are typically applied as effective mordants in the dyeing process, and therefore inevitably enter water with the continuous discharge of dyeing wastewater, causing stronger and more complex ecotoxicity to aquatic ecosystems^[112]. Moreover, the differences in physicochemical properties between organic dyes and heavy metals, make it more challenging to treat them simultaneously^[113]. Consequently, before releasing industrial effluent into the receiving water, it is vital to minimize the amount of heavy metals and organic dyes^[114].

Currently, a recommended technology for simultaneously removing two types of contaminants is to add more targeted sites to a

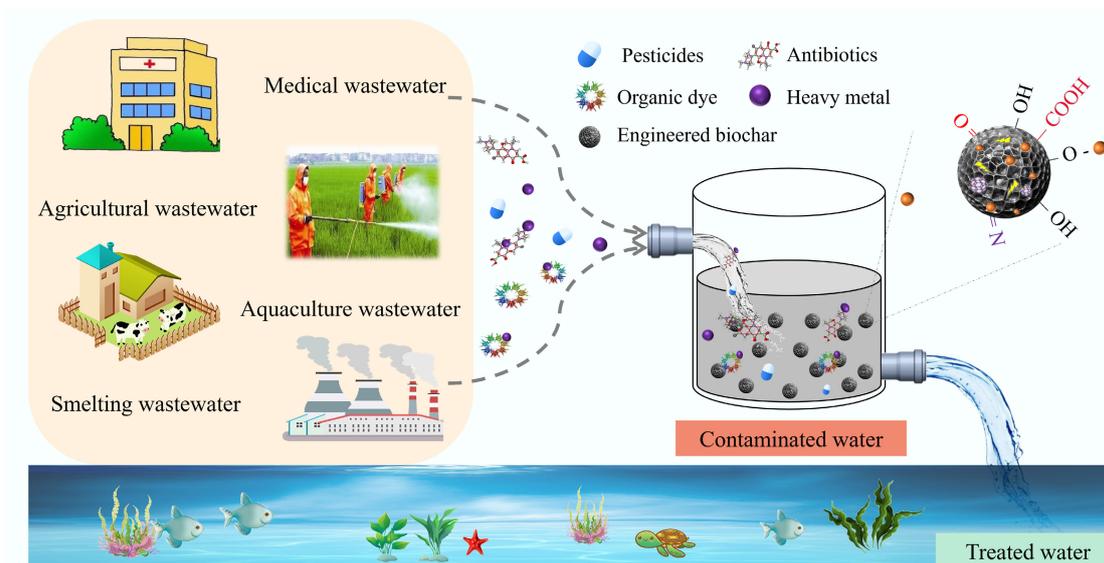


Fig. 5 Applications of engineered biochar in wastewater environment remediation.

highly effective adsorbent for a single pollutant^[115]. Engineered biochar has successfully demonstrated this remediation approach in practical applications. In a notable implementation, Zhang et al.^[116] synthesized magnetic bamboo biochar with dual-chelating agents, ethylenediamine tetraacetic acid (EDTA) and chitosan (ECMBB), which achieved simultaneous removal of Cd^{2+} , Zn^{2+} , and methyl orange (MO). Research showed that at 25 °C, the adsorption capacities of ECMBB for MO, Cd^{2+} , and Zn^{2+} were 305.4, 63.2, and 50.8 mg/g, respectively. Under identical conditions, the ECMBB adsorption capacity was 1.9, 6.1, and 5.4 times that of magnetic bamboo biochar. ECMBB effectively sequestered anionic MO through three concurrent mechanisms: π - π interactions, electrostatic forces, and hydrogen-bond formation. This engineered biochar also enhanced carboxylate functionality within metal-complexed chitosan-EDTA matrices through the strategic incorporation of amino functionalities. Notably, in the MO-metal binary system, the existence of MO remarkably enhanced the removal of Cd^{2+} and Zn^{2+} , while co-existing heavy metals had no evident impact on the MO adsorption. However, the opposite conclusion was obtained in another study. Yu et al.^[117] used KOH to activate banana peel biochar for co-removing methylene blue (MB) and Co^{2+} . The reported maximal adsorption capacities were 1,303.50 mg/g for MB and 122.39 mg/g for Co^{2+} in a single system. Their study revealed that in the binary system, the existence of MB did not affect the adsorption efficiency of Co^{2+} , but as the concentration of Co^{2+} solution increased, the negative impact on MB adsorption became more pronounced.

The above studies indicate that the interaction between heavy metals and organic dyes vary and may change due to factors such as biochar materials, preparation conditions, and initial concentrations. In particular, the chemical species of organic compounds and heavy metals in water play a critical role in their removal by biochars. Therefore, the adsorption mechanism among them is worth further investigation.

Antibiotics and heavy metals

Antibiotics (including fluoroquinolones, sulfonamides, and tetracyclines) are extensively used for their ability to prevent and treat diseases. However, due to the low absorption rate of antibiotics, only a tiny portion of them are absorbed by the body after being ingested

into human or livestock bodies. In addition, over 85% of antibiotics enter the ecological environment in the form of their parent compounds with excreta as a medium of transmission^[116]. Furthermore, antibiotics are characterized by multiple functional groups, such as $-\text{NH}_2$ and $-\text{COOH}$ for gentamicin, $-\text{OH}$ and phenol- OH for amoxicillin, as well as $\text{C}=\text{O}$ and $-\text{COOH}$ for ciprofloxacin^[118,119]. Such functionalized groups allow antibiotics to combine with other chemicals, particularly with heavy metals, to form heavy metal-antibiotic complexes^[120]. The generation of heavy metal-antibiotic complexes may alter the chemical reactivity, physicochemical characteristics, and morphology of pollutants. They may even exert a considerable influence on their ecotoxicological effects and environmental behavior^[116]. Consequently, the simultaneous removal of heavy metals and antibiotics is attracting growing research interest.

Research has reported various adsorption materials for removing heavy metals and antibiotics, reducing environmental risks. For instance, Zhou et al.^[121] prepared the ZIF-8 metal organic framework which could remove 95.4% of Cu^{2+} and 80.3% of norfloxacin. Li et al.^[122] synthesized a nano $\text{Fe}^0/\text{Fe}_3\text{O}_4$ composite loaded on blast furnace slag for *in-situ* remediation of groundwater contaminated with Cr^{6+} and oxytetracycline, and the adsorption capacities reached 38 and 95 mg/g. Azad et al.^[123] introduced a novel crosslinked/amine functionalized poly (ethylene glycol butyraldehyde)-polyacrylonitrile adsorption nanocomposite membrane with retention rates of 97.46% and 83.28% for cefotaxime and Pb^{2+} within 90 min. Although the composites reported above have good removal efficiency for antibiotics and heavy metals, their complex synthesis conditions and high cost limit their industrial application^[124].

Biochar, with its advantages of simple preparation, wide sources, and good stability, has gained increasing research attention, and has achieved good results in removing antibiotics and heavy metals^[125]. For instance, Cao et al.^[126] prepared bentonite-activated sludge biochar using a one-step pyrolysis process for co-removing norfloxacin (NOR) and Cu^{2+} . The results suggested that when the mixing ratio of bentonite and sludge was 1:2, the maximum adsorption capacities for NOR and Cu^{2+} reached 89.36 and 104.10 mg/g, respectively. Interestingly, the existence of Cu^{2+} suppressed the NOR adsorption on bentonite-activated sludge biochar and sludge biochar, and the inhibitory effect progressively enhanced as the

proportion of sludge grew. Meanwhile, the addition of NOR also reduced the adsorption efficiency of Cu^{2+} . This might be because ion competition lowers the adsorption efficiency of Cu^{2+} and NOR in the combined system. Zhao et al.^[89] also reported similar findings. However, Yan et al.^[127] obtained the opposite conclusion. The research team used wheat straw and ferrate (K_2FeO_4) as precursors to prepare iron-modified biochar (Fe-BC) for sulfadiazine (SDZ) and Cu^{2+} adsorption. The adsorption capacity of Fe-BC for SDZ and Cu^{2+} in a binary system was higher than that in a single system, which might be owing to the complexation and mutual bridging effect between SDZ and Cu^{2+} . Additionally, the loaded iron oxide particles could act as a physical barrier, preventing the Cu^{2+} and SDZ from segregating and thereby suppressing competitive adsorption.

In summary, different modification methods and pollutants can lead to different interactions, thereby promoting or inhibiting their removal efficiency. Therefore, in response to the integrated contamination of heavy metals and antibiotics, it is essential to conduct systematic research on specific pollution scenarios, rather than simply applying generalized strategies.

Other organic pollutants and heavy metals

Except for the organic pollutants listed above, the environment usually contains multiple other components, such as PAHs, phenolic compounds, microplastics (NPs), and perfluorinated compounds (PFCs). Among them, PAHs are also widespread organic pollutants in the water environment, which are the earliest discovered and studied chemical carcinogens. When wastewater contains both industrial and domestic waste as well as rainwater containing road sediments, the simultaneous presence of heavy metals and PAHs in wastewater are universal^[128]. Both of them can have detrimental impacts on the aquatic environment and can even be accumulated in the human body via the food chain because of their high toxicity and persistence. Given the importance of simultaneously removing these two types of pollutants, this topic has attracted increasing research in recent years. Lu et al.^[129] investigated whether Cu^{2+} and Cr^{6+} inhibit the acenaphthene removal efficiency in co-existing systems utilizing bamboo and rice bran biochar. They found that co-existing Cu^{2+} and Cr^{6+} both suppressed the surface adsorption of acenaphthene by biochar. This was attributed to the fact that Cu^{2+} bound directly to the oxygenated functionalized groups of biochar. Meanwhile, Cr^{6+} was reduced to Cr^{3+} , which subsequently bound to the oxygen-containing functionalized groups. Chen et al.^[130] reported a similar phenomenon.

Furthermore, studies have reported that Cr^{3+} typically coexists with bisphenol A (BPA) in polluted surface and groundwater^[131]. BPA, as a typical compound of endocrine disruptors, is widely used as a plasticizer. It can cause reproductive damage to humans and animals even at low concentrations. Engineered biochar also exhibits efficient simultaneous removal performance. For instance, Zhao et al.^[39] utilized H_3PO_4 to activate corn straw biochar for the simultaneous removal of Cr^{3+} and BPA. The findings indicated that although the presence of BPA decreased the Cr^{6+} removal efficiency, it decreased by up to 10%. No sustained decrease was observed with the enhancement of BPA concentration. The existence of Cr^{6+} improved the BPA removal efficiency, which might be caused by hydrogen bonding interaction promoted by the bridging of oxygen-containing groups from CrO_4^{2-} between BPA and biochar.

Meanwhile, NPs have become a globally recognized emerging environmental issue. There are research reports that NPs are released exponentially, seriously affecting water resource quality^[132]. In addition to containing a variety of copolymers, polymers, and chemicals, NPs can act as carriers of heavy metals in the water environment and may pose a hazard to human health and aquatic

organisms. Gao et al.^[133] examined the adsorption characteristics of NPs on heavy metals by indoor and field experiments. The findings demonstrated that Cd, Cu, and Pb might all be adsorbed by polyvinyl chloride, polypropylene, polyethylene, polyamide, and polyoxymethylene. A complementary 6-month on-site experiment revealed significant accumulation of Cr, Pb, Cd, Cu, and Mn specifically on polyvinyl chloride and polypropylene substrates.

Ganie et al.^[134] synthesized nano zero-valent iron-modified sugarcane bagasse biochar (nZVI-SBC) to explore how to effectively remove NPs and heavy metals. This engineered biochar demonstrated effective remediation capacity for diverse contaminants, including NPs and heavy metals (e.g., Cd^{2+} , Ni^{2+} , CrO_4^{2-} , and AsO_4^{3-}), with varying physicochemical properties and dimensional characteristics. It was observed that the maximum adsorption capacity of nZVI-SBC on 500 nm NPs modified with carboxylate was 90.3 mg/g, and Cd^{2+} , Ni^{2+} , CrO_4^{2-} , and AsO_4^{3-} exhibited the adsorption capacities of 44.0, 40.3, 87.8, and 47.6 mg/g. The removal mechanism of nZVI-SBC on NPs was electrostatic attraction, pore filling, and complexation, while surface complexation and co-precipitation were possible mechanisms for removing heavy metals. Currently, there is very little research on the simultaneous removal of heavy metals and NPs, and their adsorption performance and mechanism still need to be discussed. Expanding the applicability of engineered biochar to practical environments also requires a large amount of research evidence to support it.

In addition, PFCs are extensively utilized in a variety of applications, including lubricants, cleaning agents, flame retardants, and surfactants, due to their unique oleophobicity and hydrophobicity^[135], especially in the electroplating process. Therefore, high concentrations of PFCs mixed with heavy metals are often found in the wastewater discharged from electroplating plants^[136]. Yea et al.^[95] used polyaniline-activated biochar (AB@PANI) to remove perfluorooctanoic acid, perfluorooctane sulfonate, and perfluorohexane sulfonate, and studied the effect of coexisting cations (Pb^{2+} , Ca^{2+} , Mg^{2+} , Zn^{2+} , and Cd^{2+}) on their removal performance. The results indicated that these heavy metal ions could act as bridging ions to form complexes from the surface of heavy metal ion contaminants of the inner sphere adsorbent and exchange ions with AB@PANI, thus improving the removal efficiency of PFCs. However, this study only considers heavy metal ions as an influencing factor to study the removal performance of PFCs. Although it has some reference value, it cannot fully reveal the mechanism and application potential of engineered biochar for simultaneously removing PFCs and heavy metals.

Numerous factors can affect the adsorption of organic pollutants and heavy metals by engineered biochar. The adsorption performance of engineered biochar can be impacted by changes in its hydrophobicity, surface area, and pore structure, which can be brought about by varying pyrolysis temperatures and raw feedstock types. Furthermore, contaminants and environmental conditions, such as reaction temperature and pH, evidently affect the adsorption performances of engineered biochar. Therefore, it is essential to fully understand the impact of co-existing organic pollutants and heavy metals on the adsorption performance of engineered biochar.

Environmental application potential assessment of engineered biochar

Regeneration performance

The effective regeneration and recycling of engineered biochar play a decisive role in enhancing the economic viability of wastewater

treatment^[137]. Table 2 shows the regeneration performance of different biochars. To recover pollutant-laden biochar for reuse, several different types of reagents have been studied to elute heavy metals and organic pollutants from adsorbed engineered biochar. Dyes (Congo red, methylene blue, and malachite green) can be desorbed using non-ionic or cationic surfactants, alcohols, or HCl^[138,139]. Sulfamethoxazole, tetracycline, and other antibiotics can be desorbed by methanol/ethanol, NaOH, HCl, non-ionic or anionic surfactants, and complex solvents consisting of several of these reagents^[140–142]. The principle of NaOH desorption is that at high pH, anions undergo desorption. Due to the deprotonation of engineered biochar, excessive negative charges repel anions, leading to their desorption. Moreover, HCl, citric acid, NaOH, and ethylenediamine tetraacetic acid can desorb heavy metals, e.g., Cr, Cu, and Pb^[143–145]. The principle of HCl desorption is that at low pH, the surface protons and excess positive charges of engineered biochar repel cations, causing them to desorb from the surface^[146].

In binary systems, the co-existence of organic pollutants and heavy metals can affect the regeneration efficiency of engineered biochar^[147]. Given the disparate regeneration performances of organic pollutants and heavy metals, sequential recovery may represent a more advantageous strategy^[148]. Although a range of studies have reported the regeneration of engineered biochar following simultaneous adsorption, these methods demonstrate intrinsic limitations. For instance, improper handling during solvent recovery may introduce new contaminants and residues, and frequent chemical regeneration can decrease the physicochemical characteristics of the biochar^[116]. Nevertheless, there is an emergent need to further research and develop a straightforward and useful method for regenerating biochar that also addresses the removal of mixed pollutants.

Economic cost analysis

Economic cost analysis is the most crucial step in any applied research, including pollutant remediation^[149]. If the economic cost and energy demand are high, physical and chemical technologies used to remove pollutants may not be feasible^[150]. Engineered biochar is increasingly used in environmental remediation owing to its low energy

consumption, high adsorption efficiency, low cost, and ease of use in soil remediation and wastewater treatment^[151]. Production of biochar is estimated to be cheaper in comparison to commercially activated carbon, costing USD \$246 ton⁻¹ for biochar compared to about USD \$1,500 ton⁻¹ for activated carbon^[152].

Currently, there is little research on the cost analysis of engineered biochar that can simultaneously remove heavy metals and organic pollutants. However, some researchers have reported that the cost of pristine rapeseed straw biochar was USD \$0.16 kg⁻¹, but the adsorption capacity for As was extremely low (25 µg/g). After modification with H₃PO₄-FeCl₃, the adsorption capacity for As reached 960 µg/g, and the production cost was USD \$5.14 kg⁻¹, which was within the price range of other reported biochar prices^[153]. Meng et al.^[154] calculated the energy and chemical costs of MnFe₂O₄-modified sludge biochar, as well as the amount required to remove levofloxacin. The calculation results showed that its cost was approximately 0.039 USD \$/kg. In summary, the cost changes of engineered biochar are related to changes in feedstocks and production processes (such as pyrolysis temperature). Comprehensive consideration is needed when calculating costs.

The economic cost analysis of engineered biochar should not be limited to production cost, application cost, and economic benefit analysis^[155]. The production cost first involves the preparation of engineered biochar, including biomass collection, investment in pyrolysis equipment, and operating costs. Furthermore, the cost of the functionalization stage includes functionalizing agents, equipment, and energy consumption^[156,157]. The application cost primarily involves the deployment, monitoring, and maintenance of engineered biochar. Firstly, it is necessary to consider the equipment, manpower, and transportation costs for deployment and application. Secondly, to ensure the sustained effectiveness of engineered biochar, monitoring and maintenance are also necessary, which will incur certain economic expenses^[158,159]. The application of engineered biochar in aquatic environments may bring various economic benefits^[131]. Initially, it can adsorb harmful pollutants, improving water quality while minimizing the cost of water environment remediation. Additionally, through improved water parameters, engineered biochar may catalyze aquaculture sector expansion

Table 2 Regeneration performance of engineered biochar

Engineered biochars	Pollutants	Regeneration methods	Regeneration performance	Cycle number	Ref.
NaOH-modified cactus biochar	Peacock stone green Cu ²⁺ Ni ²⁺	0.1 M NaOH	The removal rate of peacock stone green decreased by 15%, and the removal rates of Cu ²⁺ and Ni ²⁺ both decreased by 16%.	6	[109]
Iron/Zinc modified wood chip biochar	TC Cu ²⁺	0.1 M NaOH	The removal rates of TC and Cu ²⁺ both exceed 89%.	3	[98]
Polyacrylic acid-modified tobacco stem biochar	Quinlorac Pb ²⁺	–	The removal rate of quinlorac was 53.8%, and the removal rate of Pb ²⁺ was 45.5%.	5	[179]
Hydroxyapatite-modified cod bone biochar	Diclofenac Fluoxetine Pb ²⁺	Deionized water	The adsorption capacity of diclofenac decreased by 11%–13%, the adsorption capacity of fluoxetine decreased by 15%–16%, and the adsorption capacity of Pb ²⁺ decreased by 1.99%.	1	[172]
EDTA/Chitosan bifunctionalized magnetic biochar	MO Cd ²⁺ Zn ²⁺	1 M NaOH 0.01 M EDTA-2Na	The removal rate of MO decreased by 16.8%, the removal rate of Cd ²⁺ decreased by 1.5%, and the removal rate of Zn ²⁺ decreased by 8.9%.	8	[116]
Potassium ferrate-activated wheat straw biochar	Cu ²⁺ SMZ	0.01 M NaOH	–	3	[127]
Ball-milled magnetic nano biochar	TC Hg ²⁺	0.2 M NaOH 0.5 M Na ₂ S	The adsorption capacities of TC and Hg ²⁺ were approximately 90.55 and 87.36 mg/g.	5	[182]
Iron/zinc-activated rice straw biochar	17β-estradiol Cu ²⁺	Ethanol Deionized water	The removal rate of 17β-estradiol and Cu ²⁺ decreased by 13.79% and 12.16%.	5	[180]
Iron/nitrogen co-doped rapeseed straw biochar	CIP Cu ²⁺	–	The adsorption capacities of CIP and Cu ²⁺ were approximately 3.67 and 3.89 mg/g.	5	[176]

and revenue enhancement^[160]. Economic viability assessment requires a systematic evaluation of production costs, implementation requirements, operational expenditures, and projected financial returns throughout the complete lifecycle of these engineered carbon-based remediation technologies.

Environmental risk assessment

Engineered biochar can efficiently remove heavy metals and organic pollutants via mechanisms including chemical bonding and physical adsorption. However, its adsorption–release dynamics remain a concern^[161]. On the one hand, engineered biochar can effectively reduce the pollution load in the environment by adsorbing pollutants. On the other hand, due to the saturation of its adsorption saturation sites of engineered biochar, excessive adsorption may result in the release of contaminants, leading to potential secondary pollution of the environment^[162,163]. Moreover, engineered biochar loaded with pollutants may have toxic effects on exposed animals, plants, crops, microorganisms, and even humans in the environment^[164,165]. In addition, previous studies have reported that engineered biochar, depending on different feedstocks, probably contains persistent free radicals and PAHs, which may also have potential adverse effects on the aquatic environment^[166].

The underlying environmental risks of engineered biochar require a comprehensive understanding and evaluation to provide reliable scientific support for environmental governance^[167]. Life cycle assessment (LCA) is a broadly applied tool for evaluating the environmental impacts of all the outputs and inputs of a product (or process) over its entire life cycle^[168]. In the assessment, inputs and outputs of each stage are quantified and summarized, and the environmental effects generated by these inputs and outputs are analyzed and evaluated. Reasonable summaries and explanations of the relevant analysis results will be made^[169].

At present, most studies focus on assessing the economic costs and environmental implications of the preparation of biochar^[170]. The system boundary is shown in Fig. 6. It defines the range from the completion of the collection of different kinds of feedstocks to the end of the application of biochar in the water environment. It contains several steps such as collection, transportation, storage, drying, and the pyrolysis process. For example, Norberto et al.^[153] aimed to investigate the environmental impact of modified rapeseed straw biochar for adsorbing As. The system boundary considered subsystems such as the collection, transportation, treatment,

and preparation of rapeseed straw biochar, but did not include the disposal of adsorbents after use. The results indicated that modified rapeseed straw biochar offers higher environmental efficiency.

However, LCA also faces challenges in evaluating the environmental and social impacts of different stages of the lifecycle of engineered biochar, as the relevant environmental indicators (such as climate change and ecotoxicity) are numerous. Whether from the perspective of their impact or from a scientific perspective, these indicators are not equal^[171]. There is not yet a consensus on which indicator has a more significant impact. Therefore, to better evaluate the lifecycle impact of engineered biochar, it is advisable to adopt a multidimensional evaluation method that comprehensively considers the weight and degree of influence of various environmental indicators, along with the influence of different social factors. This allows for a more comprehensive understanding of the true social and environmental impacts of engineered biochar, and provides a more reliable basis for formulating more reasonable policies and decisions.

Conclusions and future perspectives

The adsorption technology of engineered biochar offers a sustainable and environmentally friendly solution for treating contaminated water. Adsorbent materials based on solid wastes derived from industry, agriculture, and forestry have abundant functionalized groups, making them promising adsorbents for pollutant removal in either their pristine or functionalized forms. This paper reviews the categorization of engineered biochar and its applications in the synergistic removal of organic pollutants and heavy metals. Compared with other adsorbents, engineered biochar is renewable, biodegradable, biocompatible, and economically viable. Green, environmentally friendly, and low-cost biochar modification methods will become an inevitable trend for the co-removal of heavy metals and organic pollutants in water in the future. Moreover, various factors influence the interactions between organic contaminants and heavy metals, which are worth further exploration. Advancements in research on engineered biochar will undoubtedly lead to the emergence of new issues and challenges. Therefore, the following considerations should be pursued in future research:

(1) Explore more potential biomass feedstocks and functionalization materials. At present, the solid waste extensively applied in the

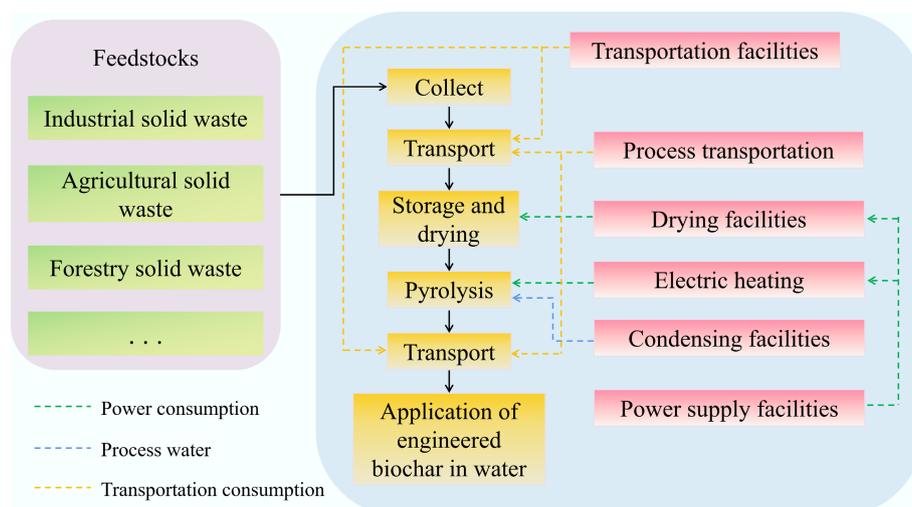


Fig. 6 System boundary of engineered biochar production process.

preparation of biochar primarily include straw, animal manure/remains, fruit peel, sludge, etc, and further types of biomass feedstocks could be explored in the future. Moreover, while deciding whether to functionalize biochar, it is essential to take into account the cost, effectiveness, and stability of the modified materials. Industrial solid wastes like phosphogypsum and electrolytic manganese slag may be taken into consideration due to their large-scale accumulation and content of metallic elements.

(2) Research on the collaborative removal mechanisms of heavy metals and organic pollutants needs to be further strengthened. The research scope can be expanded to include the interaction between emerging organic pollutants and multivalent heavy metals. The microscopic interface adsorption process can be systematically analyzed using modern advanced characterization techniques and multidisciplinary research methods. Specifically, combined with a machine learning algorithm, a prediction model for competitive adsorption of pollutants could be constructed to clarify the principles of multi-mechanism coupling by the combination of emerging technologies such as artificial intelligence, machine learning, *in-situ* real-time monitoring, and characterization, etc.

(3) The potential of engineered biochar for practical industrial applications needs to be assessed. Although studies have shown that engineered biochar can improve adsorption performance, a comprehensive and systematic evaluation of its application in actual industrial wastewater is still required. This can be achieved by investigating techniques for the removal, recycling, and regeneration of multi-component contaminants. Moreover, from the perspective of safe utilization, it is essential to clarify the interaction mechanism of engineered biochar with environmental media, such as whether the use of nanomaterials increases potential ecotoxicity and health risks.

(4) Several key factors need to be considered when applying engineered biochar in practical contexts. Firstly, although the feedstocks for biochar are inexpensive, the recovery and regeneration process after saturation is complex and costly. Secondly, the complex composition and high concentration of pollutants in the actual wastewater impose greater demands on the reusability and stability of biochar. Finally, the adsorption process of biochar does not decrease the toxicity of pollutants. Consequently, to effectively eliminate pollutants from water, it is essential to consider coupling biochar with other technologies to further convert the pollutants into harmless substances.

Author contributions

The authors confirm their contributions to the paper as follows: methodology, formal analysis: Wang N, Wang B; conceptualization: Wang B; writing – original draft preparation: Wang N; writing – review and editing: Wang B, Wang H, Wu P, Hassan M, Wang S, Zhang X. All authors reviewed the results and approved the final version of the manuscript.

Data availability

No data and materials were used for the research described in the manuscript.

Funding

This work was supported by the Key Project of Science and Technology Department of Guizhou Province (ZK[2022]016), the Special Fund for Outstanding Youth Talents of Science and Technology of Guizhou Province (YQK2023[014]), the Project of Science and Technology Department of Guizhou Province (GCC[2023]045), the Science and

Technology Support Program of Science and Technology Department of Guizhou Province (QKHZC[2025]100), and the Foreign Expert Project of the Ministry of Science and Technology (No. Y20240039).

Declarations

Conflict of interest

The authors declare no conflict of interest.

Author details

¹Key Laboratory of Karst Georesources and Environment (Guizhou University), Ministry of Education, Guiyang 550025, China; ²College of Resources and Environmental Engineering, Guizhou University, Guiyang 550025, China; ³School of Environmental and Chemical Engineering, Foshan University, Foshan 528000, China; ⁴Guangdong Provincial Key Laboratory of Integrated Agro-Environmental Pollution Control and Management, Institute of Eco-Environmental and Soil Sciences, Guangdong Academy of Sciences, Guangzhou 510650, China; ⁵College of Environmental Science and Engineering, Yangzhou University, Yangzhou 225127, China; ⁶School of Environmental Engineering, Xuzhou University of Technology, Xuzhou 221018, China

References

- [1] Chen Z, Li Y, Cai Y, Wang S, Hu B, et al. 2023. Application of covalent organic frameworks and metal-organic frameworks nanomaterials in organic/inorganic pollutants removal from solutions through sorption-catalysis strategies. *Carbon Research* 2:8
- [2] Cheng N, Wang B, Feng Q, Zhang X, Chen M. 2021. Co-adsorption performance and mechanism of nitrogen and phosphorus onto *Eupatorium adenophorum* biochar in water. *Bioresource Technology* 340:125696
- [3] Aziz FFA, Jalil AA, Hassan NS, Fauzi AA, Azami MS, et al. 2022. A review on synergistic coexisting pollutants for efficient photocatalytic reaction in wastewater remediation. *Environmental Research* 209:112748
- [4] Zou H, Zhao J, He F, Zhong Z, Huang J, et al. 2021. Ball milling biochar iron oxide composites for the removal of chromium (Cr(VI)) from water: Performance and mechanisms. *Journal of Hazardous Materials* 413:125252
- [5] Jiang Z, Chen M, Lee X, Feng Q, Cheng N, et al. 2023. Enhanced removal of sulfonamide antibiotics from water by phosphogypsum modified biochar composite. *Journal of Environmental Sciences* 130:174–186
- [6] Novikau R, Lujaniene G. 2022. Adsorption behaviour of pollutants: Heavy metals, radionuclides, organic pollutants, on clays and their minerals (raw, modified and treated): A review. *Journal of Environmental Management* 309:114685
- [7] Sousa JCG, Ribeiro AR, Barbosa MO, Pereira MFR, Silva AMT. 2018. A review on environmental monitoring of water organic pollutants identified by EU guidelines. *Journal of Hazardous Materials* 344:146–162
- [8] Aruna, Bagotia N, Sharma AK, Kumar S. 2021. A review on modified sugarcane bagasse biosorbent for removal of dyes. *Chemosphere* 268:129309
- [9] Gupta VK, Agarwal S, Ahmad R, Mirza A, Mittal J. 2020. Sequestration of toxic congo red dye from aqueous solution using ecofriendly guar gum/ activated carbon nanocomposite. *International Journal of Biological Macromolecules* 158:1310–1318
- [10] Ma Y, Liu A, Egodawatta P, McGree J, Goonetilleke A. 2017. Assessment and management of human health risk from toxic metals and polycyclic aromatic hydrocarbons in urban stormwater arising from anthropogenic activities and traffic congestion. *Science of The Total Environment* 579:202–211
- [11] Chen J, Zhang X, Bi F, Zhang X, Yang Y, et al. 2020. A facile synthesis for uniform tablet-like TiO₂/C derived from materials of institut lavoisier-125(Ti) (MIL-125(Ti)) and their enhanced visible light-driven

- photodegradation of tetracycline. *Journal of Colloid and Interface Science* 571:275–284
- [12] Khoshtinat F, Tabatabaie T, Ramavandi B, Hashemi S. 2021. Phenol removal kinetics from synthetic wastewater by activation of persulfate using a catalyst generated from shipping ports sludge. *Chemosphere* 283:131265
- [13] Zhou Y, He Z, Tao Y, Xiao Y, Zhou T, et al. 2016. Preparation of a functional silica membrane coated on Fe₃O₄ nanoparticle for rapid and selective removal of perfluorinated compounds from surface water sample. *Chemical Engineering Journal* 303:156–166
- [14] Cheng N, Wang B, Chen M, Feng Q, Zhang X, et al. 2023. Adsorption and photocatalytic degradation of quinolone antibiotics from wastewater using functionalized biochar. *Environmental Pollution* 336:122409
- [15] Rodriguez-Mozaz S, Chamorro S, Marti E, Huerta B, Gros M, et al. 2015. Occurrence of antibiotics and antibiotic resistance genes in hospital and urban wastewaters and their impact on the receiving river. *Water Research* 69:234–242
- [16] Madureira J, Barros L, Melo R, Cabo Verde S, Ferreira ICFR, et al. 2018. Degradation of phenolic acids by gamma radiation as model compounds of cork wastewaters. *Chemical Engineering Journal* 341:227–237
- [17] Liu X, Wei W, Xu J, Wang D, Song L, Ni B. 2020. Photochemical decomposition of perfluorochemicals in contaminated water. *Water Research* 186:116311
- [18] Sun S, Yao H, Fu W, Xue S, Zhang W. 2020. Enhanced degradation of antibiotics by photo-fenton reactive membrane filtration. *Journal of Hazardous Materials* 386:121955
- [19] Fu ZJ, Jiang SK, Chao XY, Zhang CX, Shi Q, et al. 2022. Removing miscellaneous heavy metals by all-in-one ion exchange-nanofiltration membrane. *Water Research* 222:118888
- [20] Li H, Tian Y, Liu W, Long Y, Ye J, et al. 2020. Impact of electrokinetic remediation of heavy metal contamination on antibiotic resistance in soil. *Chemical Engineering Journal* 400:125866
- [21] Ma X, Guo N, Ren S, Wang S, Wang Y. 2019. Response of antibiotic resistance to the co-existence of chloramphenicol and copper during bio-electrochemical treatment of antibiotic-containing wastewater. *Environment International* 126:127–133
- [22] Pan X, Gu Z, Chen W, Li Q. 2021. Preparation of biochar and biochar composites and their application in a Fenton-like process for wastewater decontamination: A review. *Science of The Total Environment* 754:142104
- [23] Crini G, Lichtfouse E. 2019. Advantages and disadvantages of techniques used for wastewater treatment. *Environmental Chemistry Letters* 17:145–155
- [24] Atun G, Ayar N, Kurtoğlu AE, Ortaboy S. 2019. A comparison of sorptive removal of anthraquinone and azo dyes using fly ash from single and binary solutions. *Journal of Hazardous Materials* 371:94–107
- [25] Wang L, Han X, Liang T, Yan X, Yang X, et al. 2022. Cosorption of Zn(II) and chlortetracycline onto montmorillonite: pH effects and molecular investigations. *Journal of Hazardous Materials* 424:127368
- [26] Du L, Zhao Y, Wang C, Zhang H, Chen Q, et al. 2020. Removal performance of antibiotics and antibiotic resistance genes in swine wastewater by integrated vertical-flow constructed wetlands with zeolite substrate. *Science of The Total Environment* 721:137765
- [27] Ai Y, Liu Y, Huo Y, Zhao C, Sun L, et al. 2019. Insights into the adsorption mechanism and dynamic behavior of tetracycline antibiotics on reduced graphene oxide (RGO) and graphene oxide (GO) materials. *Environmental Science: Nano* 6:3336–3348
- [28] Sun Y, Xu Y, Xu Y, Wang L, Liang X, et al. 2016. Reliability and stability of immobilization remediation of Cd polluted soils using sepiolite under pot and field trials. *Environmental Pollution* 208:739–746
- [29] Zhang Y, Zhao M, Cheng Q, Wang C, Li H, et al. 2021. Research progress of adsorption and removal of heavy metals by chitosan and its derivatives: A review. *Chemosphere* 279:130927
- [30] Wang F, Jin L, Guo C, Min L, Zhang P, et al. 2021. Enhanced heavy metals sorption by modified biochars derived from pig manure. *Science of The Total Environment* 786:147595
- [31] Fiyadh SS, AlSaadi MA, Jaafar WZ, AlOmar MK, Fayaed SS, et al. 2019. Review on heavy metal adsorption processes by carbon nanotubes. *Journal of Cleaner Production* 230:783–793
- [32] Lehmann J, Gaunt J, Rondon M. 2006. Bio-char sequestration in terrestrial ecosystems-A review. *Mitigation and Adaptation Strategies for Global Change* 11:403–427
- [33] Lehmann J, Joseph S. 2009. *Biochar for environmental management: science and technology*. London & Sterling: Earthscan, VA. 416 pp
- [34] Jiang T, Wang B, Hassan M. 2025. Green synthesis of natural limonite-modified biochar catalyst for peroxydisulfate activation in efficient degradation carbamazepine in water. *Journal of Environmental Chemical Engineering* 13:115522
- [35] Wei M, Wang B, Wu P, Zhang X, Chen M, et al. 2024. Electrolytic manganese residue-biochar composite for simultaneous removal of antimony and arsenic from water: adsorption performance and mechanisms. *Journal of Cleaner Production* 437:140623
- [36] Xu Q, Liu T, Li L, Liu B, Wang X, et al. 2021. Hydrothermal carbonization of distillers grains with clay minerals for enhanced adsorption of phosphate and methylene blue. *Bioresource Technology* 340:125725
- [37] Wang B, Zhao C, Feng Q, Lee X, Zhang X, et al. 2024. Biochar supported nanoscale zerovalent iron-calcium alginate composite for simultaneous removal of Mn(II) and Cr(VI) from wastewater: Sorption performance and mechanisms. *Environmental Pollution* 343:123148
- [38] Zhao R, Wang B, Zhang X, Lee X, Chen M, et al. 2022. Insights into Cr(VI) removal mechanism in water by facile one-step pyrolysis prepared coal gangue-biochar composite. *Chemosphere* 299:134334
- [39] Zhao N, Zhao C, Lv Y, Zhang W, Du Y, et al. 2017. Adsorption and coadsorption mechanisms of Cr(VI) and organic contaminants on H₃PO₄ treated biochar. *Chemosphere* 186:422–429
- [40] Zhou L, Zhu X, Chi T, Liu B, Du C, et al. 2022. Reutilization of manganese enriched biochar derived from *Phytolacca acinosa* Roxb. residue after phytoremediation for lead and tetracycline removal. *Bioresource Technology* 345:126546
- [41] Wang N, Wang B, Zhang X. 2024. TiO₂-loaded phosphogypsum-modified biochar for the removal of ofloxacin and Cu²⁺: Performance, mechanisms, and toxicity assessment. *Chemical Engineering Journal* 498:155441
- [42] Hu B, Ai Y, Jin J, Hayat T, Alsaedi A, et al. 2020. Efficient elimination of organic and inorganic pollutants by biochar and biochar-based materials. *Biochar* 2:47–64
- [43] Akash S, Rameshwar SS, Rajamohan N, Rajasimman M, Vo DN. 2024. Metal oxide nanobiochar materials to remediate heavy metal and dye pollution: a review. *Environmental Chemistry Letters* 22:2091–2112
- [44] Kaseera N, Kolar P, Hall SG. 2022. Nitrogen-doped biochars as adsorbents for mitigation of heavy metals and organics from water: a review. *Biochar* 4:17
- [45] Ravindiran G, Rajamanickam S, Janardhan G, Hayder G, Alagumalai A, et al. 2024. Production and modifications of biochar to engineered materials and its application for environmental sustainability: a review. *Biochar* 6:62
- [46] Huang Q, Song S, Chen Z, Hu B, Chen J, Wang X. 2019. Biochar-based materials and their applications in removal of organic contaminants from wastewater: state-of-the-art review. *Biochar* 1:45–73
- [47] Steiner T, Schulze K, Scharler R, Anca-Couce A. 2024. Comparison of single particle models for biomass char, chemical looping and metal oxide conversion processes. *Chemical Engineering Journal* 488:150993
- [48] Hong G, Shan R, Gu J, Huhe T, Yuan H, Chen Y. 2024. Fe-Zn bimetallic oxide functionalized biochar for enhanced adsorption of enrofloxacin in water. *Journal of Environmental Chemical Engineering* 12:112208
- [49] Dai SJ, Zhao YC, Niu DJ, Li Q, Chen Y. 2019. Preparation and reactivation of magnetic biochar by molten salt method: relevant performance for chlorine-containing pesticides abatement. *Journal of the Air & Waste Management Association* 69:58–70
- [50] Yadav A, Bagotia N, Sharma AK, Kumar S. 2021. Advances in decontamination of wastewater using biomass-based composites: a critical review. *Science of The Total Environment* 784:147108
- [51] Yap MW, Mubarak NM, Sahu JN, Abdullah EC. 2017. Microwave induced synthesis of magnetic biochar from agricultural biomass for removal of lead and cadmium from wastewater. *Journal of Industrial and Engineering Chemistry* 45:287–295

- [52] Cho DW, Chon CM, Yim GJ, Ryu J, Jo H, et al. 2023. Adsorption of potentially harmful elements by metal-biochar prepared via co-pyrolisis of coffee grounds and Nano Fe(III) oxides. *Chemosphere* 319:136536
- [53] Han H, Rafiq MK, Zhou T, Xu R, Mašek O, et al. 2019. A critical review of clay-based composites with enhanced adsorption performance for metal and organic pollutants. *Journal of Hazardous Materials* 369:780–796
- [54] Gopalan J, Butthiyappan A, Abdul Raman AA. 2022. Insight into metal-impregnated biomass based activated carbon for enhanced carbon dioxide adsorption: a review. *Journal of Industrial and Engineering Chemistry* 113:72–95
- [55] Jiang Z, Sun Z, Yang Y, Chen S, Shangguan W, et al. 2017. The role of metal oxide interactions: revisiting Pt growth on the TiO₂ surface in the process of impregnation method. *Nanoscale* 9:14272–14279
- [56] Lin L, Gao M, Qiu W, Wang D, Huang Q, et al. 2017. Reduced arsenic accumulation in indica rice (*Oryza sativa* L.) cultivar with ferromanganese oxide impregnated biochar composites amendments. *Environmental Pollution* 231:479–486
- [57] Li R, Wang JJ, Gaston LA, Zhou B, Li M, et al. 2018. An overview of carbothermal synthesis of metal-biochar composites for the removal of oxyanion contaminants from aqueous solution. *Carbon* 129:674–687
- [58] Fang L, Huang T, Lu H, Wu XL, Chen Z, et al. 2023. Biochar-based materials in environmental pollutant elimination, H₂ production and CO₂ capture applications. *Biochar* 5:42
- [59] Daud M, Hai A, Banat F, Wazir MB, Habib M, et al. 2019. A review on the recent advances, challenges and future aspect of layered double hydroxides (LDH) - containing hybrids as promising adsorbents for dyes removal. *Journal of Molecular Liquids* 288:110989
- [60] Keyikoglu R, Khataee A, Yoon Y. 2022. Layered double hydroxides for removing and recovering phosphate: recent advances and future directions. *Advances in Colloid and Interface Science* 300:102598
- [61] de Souza dos Santos GE, dos Santos Lins PV, de Magalhães Oliveira LMT, da Silva EO, Anastopoulos I, et al. 2021. Layered double hydroxides/biochar composites as adsorbents for water remediation applications: recent trends and perspectives. *Journal of Cleaner Production* 284:124755
- [62] Zubair M, Ihsanullah I, Abdul Aziz H, Azmier Ahmad M, Al-Harthi MA. 2021. Sustainable wastewater treatment by biochar/layered double hydroxide composites: progress, challenges, and outlook. *Biore-source Technology* 319:124128
- [63] Liang X, Su Y, Wang X, Liang C, Tang C, et al. 2023. Insights into the heavy metal adsorption and immobilization mechanisms of CaFe-layered double hydroxide corn straw biochar: synthesis and application in a combined heavy metal-contaminated environment. *Chemosphere* 313:137467
- [64] Bian H, Shen C, Liu W, Man YB, Wong MH, et al. 2023. An improved method of MgFe-layered double hydroxide/biochar composite synthesis. *Journal of Cleaner Production* 393:136186
- [65] Liao W, Zhang X, Shao J, Yang H, Zhang S, et al. 2022. Simultaneous removal of cadmium and lead by biochar modified with layered double hydroxide. *Fuel Processing Technology* 235:107389
- [66] Theiss FL, Ayoko GA, Frost RL. 2016. Synthesis of layered double hydroxides containing Mg²⁺, Zn²⁺, Ca²⁺ and Al³⁺ layer cations by coprecipitation methods—a review. *Applied Surface Science* 383:200–213
- [67] Thines KR, Abdullah EC, Mubarak NM, Ruthiraan M. 2017. Synthesis of magnetic biochar from agricultural waste biomass to enhancing route for waste water and polymer application: a review. *Renewable and Sustainable Energy Reviews* 67:257–276
- [68] Han L, Nie X, Wei J, Gu M, Wu W, et al. 2021. Effects of feedstock biopolymer compositions on the physicochemical characteristics of dissolved black carbon from lignocellulose-based biochar. *Science of The Total Environment* 751:141491
- [69] Hassan M, Naidu R, Du J, Qi F, Ahsan MA, et al. 2022. Magnetic responsive mesoporous alginate/ β -cyclodextrin polymer beads enhance selectivity and adsorption of heavy metal ions. *International Journal of Biological Macromolecules* 207:826–840
- [70] Nasar A, Mashkoor F. 2019. Application of polyaniline-based adsorbents for dye removal from water and wastewater – a review. *Environmental Science and Pollution Research* 26:5333–5356
- [71] Wang B, Wan Y, Zheng Y, Lee X, Liu T, et al. 2019. Alginate-based composites for environmental applications: a critical review. *Critical Reviews in Environmental Science and Technology* 49:318–356
- [72] Gao N, Du W, Zhang M, Ling G, Zhang P. 2022. Chitosan-modified biochar: Preparation, modifications, mechanisms and applications. *International Journal of Biological Macromolecules* 209:31–49
- [73] Liu Y, Shan H, Pang Y, Zhan H, Zeng C. 2023. Iron modified chitosan/coconut shell activated carbon composite beads for Cr(VI) removal from aqueous solution. *International Journal of Biological Macromolecules* 224:156–169
- [74] Vakili M, Rafatullah M, Salamatinia B, Abdullah AZ, Ibrahim MH, et al. 2014. Application of chitosan and its derivatives as adsorbents for dye removal from water and wastewater: a review. *Carbohydrate Polymers* 113:115–130
- [75] Zhou L, Liu J, Liu Z. 2009. Adsorption of platinum(IV) and palladium(II) from aqueous solution by thiourea-modified chitosan microspheres. *Journal of Hazardous Materials* 172:439–446
- [76] Rafique MI, Usman ARA, Ahmad M, Al-Wabel MI. 2021. Immobilization and mitigation of chromium toxicity in aqueous solutions and tannery waste-contaminated soil using biochar and polymer-modified biochar. *Chemosphere* 266:129198
- [77] Yap PL, Nine MJ, Hassan K, Tung TT, Tran DNH, et al. 2021. Graphene-based sorbents for multipollutants removal in water: a review of recent progress. *Advanced Functional Materials* 31:2007356
- [78] Fang Z, Gao Y, Bolan N, Shaheen SM, Xu S, et al. 2020. Conversion of biological solid waste to graphene-containing biochar for water remediation: A critical review. *Chemical Engineering Journal* 390:124611
- [79] Ashraf A, Liu G, Arif M, Mian MM, Rashid A, et al. 2022. Insights into the synthesis and application of biochar assisted graphene-based materials in antibiotic remediation. *Journal of Cleaner Production* 361:132211
- [80] Fu T, Zhang B, Gao X, Cui S, Guan CY, et al. 2023. Recent progresses, challenges, and opportunities of carbon-based materials applied in heavy metal polluted soil remediation. *Science of The Total Environment* 856:158810
- [81] Duan C, Ma T, Wang J, Zhou Y. 2020. Removal of heavy metals from aqueous solution using carbon-based adsorbents: a review. *Journal of Water Process Engineering* 37:101339
- [82] Samaraweera H, Pittman CU, Thirumalai RVKG, Hassan EB, Perez F, et al. 2021. Characterization of graphene/pine wood biochar hybrids: potential to remove aqueous Cu²⁺. *Environmental Research* 192:110283
- [83] Karunaratne TN, Oshani Nayanathara RM, Navarathna CM, Rodrigo PM, Thirumalai RVKG, et al. 2022. Pyrolytic synthesis of graphene-encapsulated zero-valent iron nanoparticles supported on biochar for heavy metal removal. *Biochar* 4:70
- [84] Yamada S. 2018. Cation- π interactions in organic synthesis. *Chemical Reviews* 118:11353–11432
- [85] Kundu D, Sharma P, Bhattacharya S, Gupta K, Sengupta S, et al. 2024. Study of methylene blue dye removal using biochar derived from leaf and stem of *Lantana camara* L. *Carbon Research* 3:22
- [86] Sun T, Pei P, Sun Y, Xu Y, Jia H. 2022. Performance and mechanism of As(III/V) removal from aqueous solution by novel positively charged animal-derived biochar. *Separation and Purification Technology* 290:120836
- [87] Jiang T, Wang B, Gao B, Cheng N, Feng Q, et al. 2023. Degradation of organic pollutants from water by biochar-assisted advanced oxidation processes: mechanisms and applications. *Journal of Hazardous Materials* 442:130075
- [88] Zhai M, Fu B, Zhai Y, Wang W, Maroney A, et al. 2023. Simultaneous removal of pharmaceuticals and heavy metals from aqueous phase via adsorptive strategy: a critical review. *Water Research* 236:119924
- [89] Zhao R, Ding W, Sun M, Yang L, Liu B, et al. 2022. Insight into the co-removal of Cu(II) and ciprofloxacin by calcite-biochar composite: enhancement and competition. *Separation and Purification Technology* 287:120487

- [90] Wang B, Gao B, Fang J. 2018. Recent advances in engineered biochar productions and applications. *Critical Reviews in Environmental Science and Technology* 47:2158–2207
- [91] Xia X, Wang J, Hu Y, Liu J, Darma AI, et al. 2022. Molecular insights into roles of dissolved organic matter in Cr(III) immobilization by coprecipitation with Fe(III) probed by STXM-ptychography and XANES spectroscopy. *Environmental Science & Technology* 56:2432–2442
- [92] Zhou Z, Zhang C, Xi M, Ma H, Jia H. 2023. Multi-scale modeling of natural organic matter-heavy metal cations interactions: Aggregation and stabilization mechanisms. *Water Research* 238:120007
- [93] Mo Z, Shi Q, Zeng H, Lu Z, Bi J, et al. 2024. Efficient removal of Cd(II) from aqueous environment by potassium permanganate-modified eucalyptus biochar. *Biomass Conversion and Biorefinery* 14:77–89
- [94] Cui H, Dong T, Hu L, Xia R, Zhou J, et al. 2022. Adsorption and immobilization of soil lead by two phosphate-based biochars and phosphorus release risk assessment. *Science of The Total Environment* 824:153957
- [95] Yea Y, Kim G, Wang D, Kim S, Yoon Y, et al. 2022. Selective sequestration of perfluorinated compounds using polyaniline decorated activated biochar. *Chemical Engineering Journal* 430:132837
- [96] Shao N, Li S, Yan F, Su Y, Liu F, et al. 2020. An all-in-one strategy for the adsorption of heavy metal ions and photodegradation of organic pollutants using steel slag-derived calcium silicate hydrate. *Journal of Hazardous Materials* 382:121120
- [97] Ma Y, Li M, Li P, Yang L, Wu L, et al. 2021. Hydrothermal synthesis of magnetic sludge biochar for tetracycline and ciprofloxacin adsorptive removal. *Bioresource Technology* 319:124199
- [98] Zhou Y, Liu X, Xiang Y, Wang P, Zhang J, et al. 2017. Modification of biochar derived from sawdust and its application in removal of tetracycline and copper from aqueous solution: adsorption mechanism and modelling. *Bioresource Technology* 245:266–273
- [99] Tufail MA, Iltaf J, Zaheer T, Tariq L, Amir MB, et al. 2022. Recent advances in bioremediation of heavy metals and persistent organic pollutants: a review. *Science of The Total Environment* 850:157961
- [100] Lee ME, Park JH, Chung JW. 2019. Comparison of the lead and copper adsorption capacities of plant source materials and their biochars. *Journal of Environmental Management* 236:118–124
- [101] Pap S, Paunovic O, Prosen H, Kraševac I, Trebše P, et al. 2023. Removal of benzotriazole derivatives by biochar: Potential environmental applications. *Environmental Pollution* 334:122205
- [102] Zhou H, Meng H, Zhao L, Shen Y, Hou Y, et al. 2018. Effect of biochar and humic acid on the copper, lead, and cadmium passivation during composting. *Bioresource Technology* 258:279–286
- [103] Trakal L, Veselská V, Šafařík I, Vítková M, Číhalová S, et al. 2016. Lead and cadmium sorption mechanisms on magnetically modified biochars. *Bioresource Technology* 203:318–324
- [104] Tan Z, Yuan S, Hong M, Zhang L, Huang Q. 2020. Mechanism of negative surface charge formation on biochar and its effect on the fixation of soil Cd. *Journal of Hazardous Materials* 384:121370
- [105] Li B, Liu X, Wang A, Tan C, Sun K, et al. 2022. Biochar with inherited negative surface charges derived from *Enteromorpha prolifera* as a promising cathode material for capacitive deionization technology. *Desalination* 539:115955
- [106] Wang RZ, Huang DL, Liu YG, Zhang C, Lai C, et al. 2020. Synergistic removal of copper and tetracycline from aqueous solution by steam-activated bamboo-derived biochar. *Journal of Hazardous Materials* 384:121470
- [107] Kumar R, Verma A, Rakib MRJ, Gupta PK, Sharma P, et al. 2023. Adsorptive behavior of micro(nano)plastics through biochar: co-existence, consequences, and challenges in contaminated ecosystems. *Science of The Total Environment* 856:159097
- [108] Tang W, Zanli BLGL, Chen J. 2021. O/N/P-doped biochar induced to enhance adsorption of sulfonamide with coexisting Cu²⁺/Cr(VI) by air pre-oxidation. *Bioresource Technology* 341:125794
- [109] Choudhary M, Kumar R, Neogi S. 2020. Activated biochar derived from *Opuntia ficus-indica* for the efficient adsorption of malachite green dye, Cu²⁺ and Ni²⁺ from water. *Journal of Hazardous Materials* 392:122441
- [110] Li F, Dai Y, Gong M, Yu T, Chen X. 2015. Synthesis, characterization of magnetic-sepiolite supported with TiO₂, and the photocatalytic performance over Cr(VI) and 2,4-dichlorophenol co-existed wastewater. *Journal of Alloys and Compounds* 638:435–442
- [111] Konaganti VK, Kota R, Patil S, Madras G. 2010. Adsorption of anionic dyes on chitosan grafted poly(alkyl methacrylate)s. *Chemical Engineering Journal* 158:393–401
- [112] Cai H, Ma K, Zhang Y, Li X, Wang W, et al. 2023. Carbonizing hollow metal-organic framework/layered double hydroxide (MOF/LDH) nanocomposite with excellent adsorption capacity for removal of Pb(II) and organic dyes from wastewater. *Carbon Research* 2:23
- [113] Zhao F, Repo E, Yin D, Meng Y, Jafari S, et al. 2015. EDTA-cross-linked β-cyclodextrin: an environmentally friendly bifunctional adsorbent for simultaneous adsorption of metals and cationic dyes. *Environmental Science & Technology* 49:10570–10580
- [114] Hou H, Zhou R, Wu P, Wu L. 2012. Removal of Congo red dye from aqueous solution with hydroxyapatite/chitosan composite. *Chemical Engineering Journal* 211–212:336–342
- [115] Skold ME, Thyne GD, Drexler JW, Macalady DL, McCray JE. 2008. Enhanced solubilization of a metal-organic contaminant mixture (Pb, Sr, Zn, and Perchloroethylene) by cyclodextrin. *Environmental Science & Technology* 42:8930–8934
- [116] Zhang H, Li R, Zhang Z. 2022. A versatile EDTA and chitosan bi-functionalized magnetic bamboo biochar for simultaneous removal of methyl orange and heavy metals from complex wastewater. *Environmental Pollution* 293:118517
- [117] Yu D, Wang L, Wu M. 2018. Simultaneous removal of dye and heavy metal by banana peels derived hierarchically porous carbons. *Journal of the Taiwan Institute of Chemical Engineers* 93:543–553
- [118] Khurana P, Pulicharla R, Kaur Brar S. 2021. Antibiotic-metal complexes in wastewaters: Fate and treatment trajectory. *Environment International* 157:106863
- [119] Ling C, Liu FQ, Xu C, Chen TP, Li AM. 2013. An integrative technique based on synergistic coremoval and sequential recovery of copper and tetracycline with dual-functional chelating resin: Roles of amine and carboxyl groups. *ACS Applied Materials & Interfaces* 5:11808–11817
- [120] Turel I. 2002. The interactions of metal ions with quinolone antibacterial agents. *Coordination Chemistry Reviews* 232:27–47
- [121] Zhou L, Li N, Owens G, Chen Z. 2019. Simultaneous removal of mixed contaminants, copper and norfloxacin, from aqueous solution by ZIF-8. *Chemical Engineering Journal* 362:628–637
- [122] Li Y, Deng M, Wang X, Wang Y, Li J, et al. 2021. In-situ remediation of oxytetracycline and Cr(VI) co-contaminated soil and groundwater by using blast furnace slag-supported nanosized Fe⁰/FeSx. *Chemical Engineering Journal* 412:128706
- [123] Azad H, Mohsennia M, Cheng C, Amini A. 2022. Cross-linked poly(vinyl butyral)/ amine-functionalized polyacrylonitrile adsorptive membrane nano-composited with CeO₂ nanoparticles for simultaneous aqueous removal of heavy metals and cefotaxime. *Chemical Engineering Journal* 435:134849
- [124] Yan L, Liu Y, Zhang Y, Liu S, Wang C, et al. 2020. ZnCl₂ modified biochar derived from aerobic granular sludge for developed microporosity and enhanced adsorption to tetracycline. *Bioresource Technology* 297:122381
- [125] Sizmur T, Fresno T, Akgül G, Frost H, Moreno-Jiménez E. 2017. Biochar modification to enhance sorption of inorganics from water. *Bioresource Technology* 246:34–47
- [126] Cao X, Meng Z, Song E, Sun X, Hu X, et al. 2022. Co-adsorption capabilities and mechanisms of bentonite enhanced sludge biochar for de-risking norfloxacin and Cu²⁺ contaminated water. *Chemosphere* 299:134414
- [127] Yan J, Zuo X, Yang S, Chen R, Cai T, et al. 2022. Evaluation of potassium ferrate activated biochar for the simultaneous adsorption of copper and sulfadiazine: competitive versus synergistic. *Journal of Hazardous Materials* 424:127435
- [128] Eshwarasinghe D, Loganathan P, Vigneswaran S. 2019. Simultaneous removal of polycyclic aromatic hydrocarbons and heavy metals

- from water using granular activated carbon. *Chemosphere* 223:616–627
- [129] Lu L, Lin Y, Chai Q, He S, Yang C. 2018. Removal of acenaphthene by biochar and raw biomass with coexisting heavy metal and phenanthrene. *Colloids and Surfaces A: Physicochemical and Engineering Aspects* 558:103–109
- [130] Chen C, Zhou W, Lin D. 2015. Sorption characteristics of N-nitrosodimethylamine onto biochar from aqueous solution. *Biore-source Technology* 179:359–366
- [131] Bautista-Toledo MI, Rivera-Utrilla J, Ocampo-Pérez R, Carrasco-Marín F, Sánchez-Polo M. 2014. Cooperative adsorption of bisphenol-A and chromium(III) ions from water on activated carbons prepared from olive-mill waste. *Carbon* 73:338–350
- [132] Liu S, Huang J, Zhang W, Shi L, Yi K, et al. 2022. Microplastics as a vehicle of heavy metals in aquatic environments: a review of adsorption factors, mechanisms, and biological effects. *Journal of Environmental Management* 302:113995
- [133] Gao F, Li J, Sun C, Zhang L, Jiang F, et al. 2019. Study on the capability and characteristics of heavy metals enriched on microplastics in marine environment. *Marine Pollution Bulletin* 144:61–67
- [134] Ahmad Ganie Z, Khandelwal N, Choudhary A, Darbha GK. 2023. Clean water production from plastic and heavy metal contaminated waters using redox-sensitive iron nanoparticle-loaded biochar. *Environmental Research* 235:116605
- [135] Elanchezhiyan SS, Muthu Prabhu S, Karthikeyan P, Park CM. 2021. Efficient and selective sequestration of perfluorinated compounds and hexavalent chromium ions using a multifunctional spinel matrix decorated carbon backbone N-rich polymer and their mechanistic investigations. *Journal of Molecular Liquids* 326:115336
- [136] Badruddoza AZM, Bhattarai B, Suri RPS. 2017. Environmentally friendly β -cyclodextrin-ionic liquid polyurethane-modified magnetic sorbent for the removal of PFOA, PFOS, and Cr(VI) from water. *ACS Sustainable Chemistry & Engineering* 5:9223–9232
- [137] Alsawy T, Rashad E, El-Qelish M, Mohammed RH. 2022. A comprehensive review on the chemical regeneration of biochar adsorbent for sustainable wastewater treatment. *NPJ Clean Water* 5:29
- [138] Maiti P, Mangsatabam M, Chatterjee A, Siddiqi H, Mishra A, et al. 2024. In-situ synthesis of efficient ZnCl₂ doped pyrolyzed biochar for adsorptive remediation of organic dyes: performance evaluation, mass transfer and mechanism. *Separation and Purification Technology* 329:125096
- [139] Singh M, Ahsan M, Pandey V, Singh A, Mishra D, et al. 2022. Comparative assessment for removal of anionic dye from water by different waste-derived biochar vis a vis reusability of generated sludge. *Biochar* 4:13
- [140] Chakhtouna H, Benzeid H, Zari N, Qaiss Aek, Bouhfid R. 2023. Microwave-assisted synthesis of MIL-53(Fe)/biochar composite from date palm for ciprofloxacin and ofloxacin antibiotics removal. *Separation and Purification Technology* 308:122850
- [141] Gao J, Zhou Y, Yang X, Yao Y, Qi J, et al. 2024. Dyeing sludge-derived biochar for efficient removal of antibiotic from water. *Science of The Total Environment* 912:169035
- [142] Li H, Hu J, Meng Y, Su J, Wang X. 2017. An investigation into the rapid removal of tetracycline using multilayered graphene-phase biochar derived from waste chicken feather. *Science of The Total Environment* 603–604:39–48
- [143] Hassan M, Wang B, Wu P, Wang S. 2024. Engineered biochar for in-situ and ex-situ remediation of contaminants from soil and water. *Science of The Total Environment* 957:177384
- [144] Ifthikar J, Jiao X, Ngambia A, Wang T, Khan A, et al. 2018. Facile one-pot synthesis of sustainable carboxymethyl chitosan-sewage sludge biochar for effective heavy metal chelation and regeneration. *Biore-source Technology* 262:22–31
- [145] Wu Y, Wang Z, Yan Y, Zhou Y, Huma B, et al. 2024. Recovery and regeneration of water-hardened magnetic composite biochar sphere for the removal of multiple heavy metals in contaminated soils. *Journal of Cleaner Production* 450:141906
- [146] Li Y, Yu H, Liu L, Yu H. 2021. Application of co-pyrolysis biochar for the adsorption and immobilization of heavy metals in contaminated environmental substrates. *Journal of Hazardous Materials* 420:126655
- [147] Janković B, Manić N, Dodevski V, Radović I, Pijović M, et al. 2019. Physico-chemical characterization of carbonized apricot kernel shell as precursor for activated carbon preparation in clean technology utilization. *Journal of Cleaner Production* 236:117614
- [148] Chen J, Bao C, Chen M, Wang Y, Xu X, et al. 2023. β -cyclodextrin-scaffolded crosslinked poly(ionic liquid)s for ultrafast removal of multiple pollutants: insight into adsorption performance and mechanism. *Chemical Engineering Journal* 464:142526
- [149] Shaheen SM, Natasha, Mosa A, El-Naggar A, Faysal Hossain M, et al. 2022. Manganese oxide-modified biochar: production, characterization and applications for the removal of pollutants from aqueous environments – a review. *Biore-source Technology* 346:126581
- [150] Balakrishnan A, Chinthala M. 2022. Comprehensive review on advanced reusability of g-C₃N₄ based photocatalysts for the removal of organic pollutants. *Chemosphere* 297:134190
- [151] Gautam RK, Goswami M, Mishra RK, Chaturvedi P, Awashthi MK, et al. 2021. Biochar for remediation of agrochemicals and synthetic organic dyes from environmental samples: A review. *Chemosphere* 272:129917
- [152] Ahmad M, Lee SS, Dou X, Mohan D, Sung JK, et al. 2012. Effects of pyrolysis temperature on soybean stover- and peanut shell-derived biochar properties and TCE adsorption in water. *Biore-source Technology* 118:536–544
- [153] Norberto J, Zoroufchi Benis K, McPhedran KN, Soltan J. 2023. Microwave activated and iron engineered biochar for arsenic adsorption: Life cycle assessment and cost analysis. *Journal of Environmental Chemical Engineering* 11:109904
- [154] Meng X, Song T, Zhang C, Wang H, Ge M, et al. 2023. Magnetic MnFe₂O₄ nanoparticles anchored on sludge-derived biochar in activating peroxydisulfate for levofloxacin degradation: Mechanism, degradation pathways and cost analysis. *Journal of Environmental Chemical Engineering* 11:110241
- [155] Biard PF, Coudon A, Couvert A, Giraudet S. 2016. A simple and time-saving method for the mass-transfer assessment of solvents used in physical absorption. *Chemical Engineering Journal* 290:302–311
- [156] Das S, Rudra Paul S, Debnath A. 2023. Fabrication of biochar from jarul (*Lagerstroemia speciosa*) seed hull for ultrasound aided sequestration of ofloxacin from water: Phytotoxic assessments and cost analysis. *Journal of Molecular Liquids* 387:122610
- [157] Gutkoski JP, Schneider EE, Michels C. 2024. How effective is biological activated carbon in removing micropollutants? A comprehensive review. *Journal of Environmental Management* 349:119434
- [158] Alam MS, Gorman-Lewis D D, Chen N, Flynn SL, Ok YS, et al. 2018. Thermodynamic analysis of Nickel(II) and Zinc(II) adsorption to biochar. *Environmental Science & Technology* 52:6246–6255
- [159] Amir Afshar H, Ghaee A. 2016. Preparation of aminated chitosan/alginate scaffold containing halloysite nanotubes with improved cell attachment. *Carbohydrate Polymers* 151:1120–1131
- [160] Pandit NR, Mulder J, Hale SE, Zimmerman AR, Pandit BH, et al. 2018. Multi-year double cropping biochar field trials in Nepal: Finding the optimal biochar dose through agronomic trials and cost-benefit analysis. *Science of The Total Environment* 637–638:1333–1341
- [161] Besseling E, Redondo-Hasselerharm P, Foekema EM, Koelmans AA. 2019. Quantifying ecological risks of aquatic micro- and nanoplastic. *Critical Reviews in Environmental Science and Technology* 49:32–80
- [162] Tapia-Orozco N, Santiago-Toledo G, Barrón V, Espinosa-García AM, García-García JA, et al. 2017. Environmental epigenomics: current approaches to assess epigenetic effects of endocrine disrupting compounds (EDCs) on human health. *Environmental Toxicology and Pharmacology* 51:94–99
- [163] Wu Y, Song S, Chen X, Shi Y, Cui H, et al. 2023. Source-specific ecological risks and critical source identification of PPCPs in surface water: Comparing urban and rural areas. *Science of The Total Environment* 854:158792
- [164] Zhang Y, Chen Z, Xu W, Liao Q, Zhang H, et al. 2020. Pyrolysis of various phytoremediation residues for biochars: Chemical forms and environmental risk of Cd in biochar. *Biore-source Technology* 299:122581
- [165] Zong Y, Chen H, Malik Z, Xiao Q, Lu S. 2022. Comparative study on the potential risk of contaminated-rice straw, its derived biochar and

- phosphorus modified biochar as an amendment and their implication for environment. *Environmental Pollution* 293:118515
- [166] Odinga ES, Waigi MG, Gudda FO, Wang J, Yang B, et al. 2020. Occurrence, formation, environmental fate and risks of environmentally persistent free radicals in biochars. *Environment International* 134:105172
- [167] Yang YY, Toor GS, Wilson PC, Williams CF. 2017. Micropollutants in groundwater from septic systems: transformations, transport mechanisms, and human health risk assessment. *Water Research* 123:258–267
- [168] Mahmud R, Moni SM, High K, Carbajales-Dale M. 2021. Integration of techno-economic analysis and life cycle assessment for sustainable process design – a review. *Journal of Cleaner Production* 317:128247
- [169] Hussin F, Hazani NN, Khalil M, Aroua MK. 2023. Environmental life cycle assessment of biomass conversion using hydrothermal technology: a review. *Fuel Processing Technology* 246:107747
- [170] Moreira MT, Noya I, Feijoo G. 2017. The prospective use of biochar as adsorption matrix – a review from a lifecycle perspective. *Bioresource Technology* 246:135–141
- [171] Ren B, Shi X, Jin X, Wang XC, Jin P. 2021. Comprehensive evaluation of pharmaceuticals and personal care products (PPCPs) in urban sewers: Degradation, intermediate products and environmental risk. *Chemical Engineering Journal* 404:127024
- [172] Piccirillo C, Moreira IS, Novais RM, Fernandes AJS, Pullar RC, et al. 2017. Biphasic apatite-carbon materials derived from pyrolysed fish bones for effective adsorption of persistent pollutants and heavy metals. *Journal of Environmental Chemical Engineering* 5:4884–4894
- [173] Dutta DP, Nath S. 2018. Low cost synthesis of SiO₂/C nanocomposite from corn cobs and its adsorption of uranium (VI), chromium (VI) and cationic dyes from wastewater. *Journal of Molecular Liquids* 269:140–151
- [174] Le Minh Tri N, Thang PQ, Van Tan L, Huong PT, Kim J, et al. 2020. Removal of phenolic compounds from wastewaters by using synthesized Fe-nano zeolite. *Journal of Water Process Engineering* 33:101070
- [175] Deng J, Li X, Wei X, Liu Y, Liang J, et al. 2020. Hybrid silicate-hydrochar composite for highly efficient removal of heavy metal and antibiotics: coadsorption and mechanism. *Chemical Engineering Journal* 387:124097
- [176] Yao B, Zeng W, Núñez-Delgado A, Zhou Y. 2023. Simultaneous adsorption of ciprofloxacin and Cu²⁺ using Fe and N co-doped biochar: competition and selective separation. *Waste Management* 168:386–395
- [177] Song Z, Liu Y, Liu L, Yang C, Tian W, et al. 2024. Reusable magnetically-modified *Enteromorpha prolifera*-based biochar hydrogels: competitive removal mechanism for metal-organic dye composite contaminants. *Carbon Research* 3:18
- [178] da Rocha HD, Reis ES, Ratkovski GP, da Silva RJ, Gorza FDS, et al. 2020. Use of PMMA/(rice husk ash)/polypyrrole membranes for the removal of dyes and heavy metal ions. *Journal of the Taiwan Institute of Chemical Engineers* 110:8–20
- [179] Li R, Wen Y, Liu M, Su L, Wang Y, et al. 2022. Simultaneous removal of organic inorganic composite contaminants by in situ double modified biochar: performance and mechanisms. *Journal of the Taiwan Institute of Chemical Engineers* 139:104523
- [180] Yin Z, Liu Y, Liu S, Jiang L, Tan X, et al. 2018. Activated magnetic biochar by one-step synthesis: Enhanced adsorption and coadsorption for 17β-estradiol and copper. *Science of The Total Environment* 639:1530–1542
- [181] Qian L, Long Y, Li H, Wei Z, Liang C, et al. 2023. Unveiling the role of biochar in simultaneous removal of hexavalent chromium and trichloroethylene by biochar supported nanoscale zero-valent iron. *Science of The Total Environment* 889:164243
- [182] Li R, Zhang Y, Deng H, Zhang Z, Wang JJ, et al. 2020. Removing tetracycline and Hg(II) with ball-milled magnetic nanobiochar and its potential on polluted irrigation water reclamation. *Journal of Hazardous Materials* 384:121095



Copyright: © 2025 by the author(s). Published by Maximum Academic Press, Fayetteville, GA. This article is an open access article distributed under Creative Commons Attribution License (CC BY 4.0), visit <https://creativecommons.org/licenses/by/4.0/>.